

Superfluid weight of strongly inhomogeneous superconductors

Jonathan Schirmer^{1,2} and Enrico Rossi¹

¹*Department of Physics, William & Mary, Williamsburg, Virginia 23187, USA*

²*Department of Physics, 104 Davey Lab, The Pennsylvania State University, University Park, Pennsylvania 16802, USA*



(Received 1 July 2025; revised 1 October 2025; accepted 7 October 2025; published 3 November 2025)

In this work, we obtain the superfluid weight of strongly inhomogeneous superconductors. We find that, in general, the response of the superconductor's pairing potential to the perturbing vector potential is essential to obtain the correct value of the superfluid weight. We consider two exemplary cases: the case when strong inhomogeneities in the pairing potential are induced by a periodic potential, and the case when superconducting vortices are induced by an external magnetic field. For both cases we show that the correction to the superfluid weight due to the response of the paring potential to the perturbing vector potential can be significant, it must be included to obtain quantitatively correct results, and that for the case when vortices are present the expression of the superfluid weight that does not include such correction returns qualitatively wrong results. The results are directly relevant for superconducting states in moiré multilayer where the almost inevitable spatial variations of the magic angle and the proximity of superconductivity to anisotropic phases induce inhomogeneities in the pairing potential, and to the efforts to optimally pin superconducting vortices to achieve large superconducting critical currents.

DOI: [10.1103/9gc8-q16z](https://doi.org/10.1103/9gc8-q16z)

The Meissner effect is the hallmark signature of superconductivity. It is described by the London equation $J_\mu = D_{\mu\nu}^{(s)} A_\nu$ where J_μ is the μ component of the charge current, A_ν is the ν component of a static, transverse, long-wavelength vector potential, and $D_{\mu\nu}^{(s)}$ is the superfluid weight tensor. $D_{\mu\nu}^{(s)}$ can be seen as the key quantity that characterizes a superconductor [1,2]. In two dimensions (2D) $D_{\mu\nu}^{(s)}$ is also the quantity that fixes the critical temperature, T_{BKT} , at which the Berezinskii-Kosterlitz-Thouless (BKT) [3,4] transition, between superconducting and normal phase, takes place. For an isotropic superconductor with an isolated parabolic band crossing the Fermi energy in the normal phase, at zero temperature, we have the conventional result $\text{Tr}[D_{\mu\nu}^{(s)}]/d = e^2 n/m^*$, where d is the number of dimensions, e is the elementary charge, n is the electron density, and m^* is the effective mass. The realization of superconducting states in magic-angle twisted bilayer graphene [5–15], for which the bands are extremely flat so that $m^* \rightarrow \infty$, has made clear the limitations of the conventional result. In recent years, more general expressions for $D_{\mu\nu}^{(s)}$ accounting for the effect of quantum geometry in multiband superconductors have been obtained [16–32]. These formulations show how, in flat-band systems like twisted bilayer graphene, the contribution to $D_{\mu\nu}^{(s)}$ arising from the quantum geometry can be dominant [33–38]. The strong interest in $D_{\mu\nu}^{(s)}$ is also evidenced by the recent experiments that have been realized to measure it directly [39–43].

In many cases of interest, the pairing potential Δ cannot be assumed to be spatially uniform. This is the case, for instance, when disorder is present [22,44–48]. It is the situation typically encountered in moiré multilayers due to the almost unavoidable presence of spatial variations of the twist angle [49] and the evidence that the superconducting state might be nematic [50]. Strong inhomogeneities have been observed to also significantly affect the superfluid state of iron-based

superconductors, as demonstrated in scanning tunneling microscopy experiments on FeTeSe [51], and are a feature of charge-density-wave materials like Pd-intercalated ErTe_3 in which anomalous superfluid density has been measured [52]. In addition, the correct, and quantitative, theory for the interplay of superfluidity and inhomogeneities is essential for the description of superconductors with vortices. We find the surprising result that in the presence of an unpinned vortex lattice the superfluid weight is zero. Our approach, based on linear response theory, provides a clear explanation for such a striking result, a result that before our work could not be understood, and could only be gleaned from a careful analysis of Monte Carlo simulations [53,54].

The presence of spatial inhomogeneities mixes the system's response to the longitudinal and transverse components of an external vector potential, a fact that makes the calculation of $D_{\mu\nu}^{(s)}$ more challenging [55]. The reason is that, whereas the BCS mean-field treatment, within the linear response approximation, returns the correct response of a superconducting system to a transverse vector field [1,2,56], it is known to return an incorrect, gauge-dependent, response to a longitudinal vector field [56]. This issue was addressed by several papers [57–66] that pointed out that for the general case, gauge invariance is restored by taking into account the vertex corrections for Δ , the so called collective-mode contributions, i.e., by including the response of Δ to the vector field \mathbf{A} . Later works considered the role of such contributions for specific cases [26,67–74]. In Ref. [20], an expression for $D_{\mu\nu}^{(s)}$ was obtained that showed the importance of such contributions to restore the independence with respect to the position of the orbitals of the long-wavelength, zero frequency electromagnetic response of a superconductor. In this work, we present a theoretical treatment for the calculation of $D_{\mu\nu}^{(s)}$ that overcomes the limitations of previous works. The treatment presented is

very general, as it does not require uniform pairing; isolated band limit; spin rotational symmetry; or time-reversal symmetry, and it is valid also for the challenging case when the phase of Δ varies rapidly in space. This generality allows the use of our treatment to calculate the superfluid weight of two very important classes of superconductors: topological superconductors and superconductors with vortices. The formalism is valid for any multiband superconductor and includes quantum-geometric contributions. To verify the accuracy of our expression, we compare its predictions to the results obtained by calculating, via a numerical self-consistent approach, the free energy, F , as a function of the perturbing field \mathbf{A} and then $D_{\mu\nu}^{(s)}$ as the second derivative of F with respect to \mathbf{A} : $D_s^{\mu\nu} = (1/V)d^2F/dA_\mu dA_\nu$, where V is the system's volume. We do this for two important exemplary cases: the case when strong inhomogeneities in Δ are induced by a periodic superlattice potential applied to a 2D superconductor, and the case when superconducting vortices are induced by an external magnetic field perpendicular to a 2D superconductor. In both cases we find that the results obtained by numerically calculating the second derivative with respect to \mathbf{A} of the free energy are the same as the ones obtained using the derived expression, but can be significantly different from the ones obtained using the expressions for $D_{\mu\nu}^{(s)}$ available in the literature that do not take into account the presence of inhomogeneities. For the case when vortices are present, the expression of $D_{\mu\nu}^{(s)}$ that does not include the response of Δ to \mathbf{A} returns a qualitatively wrong result—it erroneously predicts a finite value of $D_{\mu\nu}^{(s)}$ even for an infinite 2D array of unpinned vortices, in contrast to the expression that we present, that correctly returns $D_s^{\mu\nu} = 0$ for this situation [53,54,75].

We describe the superconducting state using a Bogoliubov-de Gennes (BdG) effective mean field Hamiltonian \hat{H}_{BdG} . Given that the goal of this work is to obtain the correct response of inhomogeneous superconductors to an external vector field, and not the identification of the many-body ground state, the use of the BdG approach is very pragmatic: it allows the modeling of any superconducting state taking as inputs from experiments the values of the parameters entering the model. For concreteness, we consider a superconductor with s -wave pairing originating from an on-site attractive interaction of strength $U > 0$. For such a system,

$$\begin{aligned} \hat{H}_{\text{BdG}} = & - \sum_{j\ell\sigma} t_j^\ell c_{j+\beta_j^\ell, \sigma}^\dagger c_{j, \sigma} - \sum_{j\sigma} \frac{1}{2} (\mu - V_j) c_{j, \sigma}^\dagger c_{j, \sigma} \\ & - \sum_j \left[\Delta_j c_{j, \uparrow}^\dagger c_{j, \downarrow}^\dagger - \frac{|\Delta_j|^2}{2U} \right] + \text{H.c.}, \end{aligned} \quad (1)$$

where the subscript j is shorthand for the position vector \mathbf{r}_j , $\sigma = \uparrow, \downarrow$ is the spin index, t_j^ℓ is the hopping amplitude at position \mathbf{r}_j along the bond β_j^ℓ , $c_{j, \sigma}^\dagger$ ($c_{j, \sigma}$) is the creation (annihilation) operator for an electron at position \mathbf{r}_j with spin σ , μ is the chemical potential, V_j is an applied potential, and Δ_j is the pairing potential at position \mathbf{r}_j obtained from the self-consistent equation $\Delta_j = U \langle c_{j, \downarrow} c_{j, \uparrow} \rangle$, where the angle brackets denote equilibrium expectation values at temperature T . In general, the lattice can have a basis and so $\mathbf{r}_j = \mathbf{R}_i + \mathbf{b}_m$, where $\{\mathbf{R}_i\}$ are the position vectors that identify the lattice and \mathbf{b}_m are the vectors for the positions of the basis elements

within the primitive cell. β_j^ℓ are bond vectors that connect sites within, and between, primitive cells, making the expression of \hat{H}_{BdG} , Eq. (1), very general. In the remainder, the primitive cell is chosen so that $\Delta(\mathbf{r}_j) = \Delta(\mathbf{r}_j + \mathbf{R}_i)$, and therefore, when Δ is inhomogeneous, can be much larger than the crystal's primitive cell.

$D_{\mu\nu}^{(s)}$ relates the strength of the charge current $\hat{\mathbf{J}}$ to a static, transverse, vector field \mathbf{A} with zero parallel momentum \mathbf{q}_\parallel , and perpendicular momentum $\mathbf{q}_\perp \rightarrow 0$ [1]: $\langle \hat{J}_\mu \rangle = D_{\mu\nu}^{(s)} A_\nu (\mathbf{q}_\parallel = 0, \mathbf{q}_\perp \rightarrow 0, \omega = 0)$, where $\langle \hat{J}_\mu \rangle$ is the expectation value of the μ component of the current, and ω the frequency of the field \mathbf{A} . $D_{\mu\nu}^{(s)}$ can therefore be obtained by calculating the linear response of $\hat{\mathbf{J}}$ to a transverse vector field \mathbf{A} . For a tight-binding model, the presence of the field \mathbf{A} can effectively be taken into account by introducing a Peierls phase for the hopping parameters: $t_j^\ell \rightarrow t_j^\ell e^{i\mathbf{A} \cdot \beta_j^\ell}$. In addition, it can induce a change in the pairing field that, as we will show, cannot be neglected for inhomogeneous superconductors. Taking this into account, as was done in Ref. [20], using $\hat{J}_\mu = -\delta \hat{H}_{\text{BdG}} / \delta A_\mu$, we find

$$\begin{aligned} \hat{J}_\mu(\mathbf{r}_j) = & \sum_{\ell, \sigma} (i\beta_j^\ell)_\mu t_j^\ell e^{i\mathbf{A}(\mathbf{r}_j, t) \cdot \beta_j^\ell} c_{j+\beta_j^\ell, \sigma}^\dagger c_{j, \sigma} + \text{H.c.} \\ & + \sum_{j'} \left[\frac{\delta \Delta_{j'}}{\delta A_\mu(\mathbf{r}_j)} c_{j', \uparrow}^\dagger c_{j', \downarrow}^\dagger - \frac{1}{2U} \frac{\delta |\Delta_{j'}|^2}{\delta A_\mu(\mathbf{r}_j)} + \text{H.c.} \right]. \end{aligned} \quad (2)$$

To first order in \mathbf{A} , we have

$$\hat{J}_\mu = \hat{J}_\mu^{Kp} + \hat{T}_{\mu\nu}^K A^\nu + \hat{J}_\mu^{\Delta p} + \hat{T}_{\mu\nu}^\Delta A^\nu, \quad (3)$$

where \hat{J}_μ^{Kp} , $\hat{T}_{\mu\nu}^K A^\nu$ are the paramagnetic and diamagnetic currents, respectively, arising from the kinetic energy part of the BdG Hamiltonian, and $\hat{J}_\mu^{\Delta p}$, $\hat{T}_{\mu\nu}^\Delta A^\nu$ the paramagnetic and diamagnetic currents due to the change of Δ_j induced by \mathbf{A} . $\hat{T}_{\mu\nu}^\Delta A^\nu$ does not contribute to $\langle \hat{J}_\mu \rangle$ and to $D_{\mu\nu}^{(s)}$ —see the Supplemental Material (SM) [76]—and so we can neglect it. $\hat{J}_\mu^{\Delta p}$ is given by the second line of Eq. (2) by evaluating the variational derivatives at $\mathbf{A} = 0$. $\hat{J}_\mu^{\Delta p}$ also does not contribute to $\langle \hat{J}_\mu \rangle$, but it does contribute to $D_{\mu\nu}^{(s)}$. As we show below, its contribution to $D_{\mu\nu}^{(s)}$ is critical when Δ is not homogeneous.

To obtain the current response to a vector field with vanishing momentum \mathbf{q} , it is convenient to express the current in momentum space. By performing the Fourier transform with respect to \mathbf{R}_i , we can write

$$c_{\mathbf{R}_i + \mathbf{b}_m, \sigma} = \frac{1}{\sqrt{N_c}} \sum_{\mathbf{k}} c_{m\sigma}(\mathbf{k}) e^{i\mathbf{k} \cdot \mathbf{b}_m} e^{i\mathbf{k} \cdot \mathbf{R}_i}, \quad (4)$$

where $c_{m\sigma}(\mathbf{k})$ [$c_{m\sigma}^\dagger(\mathbf{k})$] is the creation (annihilation) operator for an electron in the state $|\mathbf{k}m\sigma\rangle$ with momentum \mathbf{k} , orbital m , and spin σ . The operator $c(\mathbf{k})_{m, \sigma}$ is defined apart from an overall phase factor. In writing Eq. (4) we have chosen this overall phase factor to be $e^{i\mathbf{k} \cdot \mathbf{b}_m}$, given that this choice allows us to write the full paramagnetic current operator, in momentum space, in the limit $\mathbf{q} \rightarrow 0$, in the compact form

$$\hat{J}_\mu^p(\mathbf{q} \rightarrow 0) = \frac{1}{N_c} \sum_{\mathbf{k}mm'} \psi_m^\dagger(\mathbf{k}) I_{mm'\mu}(\mathbf{k}) \psi_{m'}(\mathbf{k}) + C, \quad (5)$$

where N_c is the number of unit cells, $\psi_m^\dagger(\mathbf{k}) = (c_{m\uparrow}^\dagger(\mathbf{k}), c_{m\downarrow}^\dagger(\mathbf{k}))$, C is a constant, and

$$I_{mm';\mu}(\mathbf{k}) = \begin{pmatrix} \frac{\partial H_{mm'}}{\partial k_\mu} \Big|_{\mathbf{k}} & \frac{\delta \Delta_m}{\delta A_\mu} \Big|_0 \delta_{mm'} \\ \frac{\delta \Delta_m^*}{\delta A_\mu} \Big|_0 \delta_{mm'} & -\frac{\partial H_{mm'}}{\partial k_\mu} \Big|_{-\mathbf{k}} \end{pmatrix} \quad (6)$$

with $\{H_{mm'}(\mathbf{k})\}$ the matrix elements, in the basis $\{|km\sigma\rangle\}$, of the normal state Hamiltonian, \hat{H} , and $\delta \Delta_m/\delta A_\mu|_0 \equiv \delta \Delta_m/\delta A_\mu(\mathbf{q} \rightarrow 0)|_{\mathbf{A}=0}$.

By setting the off-diagonal terms in $I_{mm';\mu}(\mathbf{k})$ equal to 0 we obtain the matrix $I_{mm';\mu}^K(\mathbf{k})$ that, when inserted in Eq. (5), returns the expression of $\hat{J}_\mu^{K,p}$ in the limit $\mathbf{q} \rightarrow 0, \omega = 0$. For the operator $\hat{T}_{\mu\nu}^K A^\nu$, we obtain

$$\begin{aligned} \hat{T}_{\mu\nu}^K(\mathbf{q}) = -\sum_{m,\ell,\sigma,\mathbf{k}} \frac{(\beta_m^\ell)_\mu (\beta_m^\ell)_\nu}{N_c} & [t_m^\ell e^{-i\mathbf{k}\cdot\beta_m^\ell} c_{m+\beta_m^\ell,\sigma}^\dagger(\mathbf{k}) c_{m\sigma}(\mathbf{k}+\mathbf{q}) \\ & + t_m^\ell e^{i(\mathbf{k}+\mathbf{q})\cdot\beta_m^\ell} c_{m\sigma}^\dagger(\mathbf{k}) c_{m+\beta_m^\ell,\sigma}(\mathbf{k}+\mathbf{q})]. \end{aligned} \quad (7)$$

The superfluid weight is given by the sum of the paramagnetic current response $\Pi_{\mu\nu}(\mathbf{q} \rightarrow 0, \omega = 0)$ and the expectation value of the operator $\hat{T}_{\mu\nu}^K$:

$$D_{\mu\nu}^{(s)} = \Pi_{\mu\nu}(\mathbf{q} \rightarrow 0, \omega = 0) + \langle \hat{T}_{\mu\nu}^K \rangle. \quad (8)$$

We have

$$\Pi_{\mu\nu}(\mathbf{q}, 0) = \frac{i}{N_c} \int_0^\infty dt \langle [\hat{J}_\mu^{K,p}(\mathbf{q}, t), \hat{J}_\nu^p(-\mathbf{q}, 0)] \rangle. \quad (9)$$

Notice that by replacing in Eq. (9) $\hat{J}_\nu^p(-\mathbf{q}, 0)$ with $\hat{J}_\nu^{K,p}(-\mathbf{q}, 0)$ we recover the expression of Π that neglects the effect on Δ of \mathbf{A} . In the limit $\mathbf{q} \rightarrow 0, \omega = 0$, we find

$$\begin{aligned} \Pi_{\mu\nu}(\mathbf{q} \rightarrow 0, 0) = \frac{1}{N_c} \sum_{\mathbf{k},ab} \frac{n_F(E_a(\mathbf{k})) - n_F(E_b(\mathbf{k}))}{E_a(\mathbf{k}) - E_b(\mathbf{k})} \\ \times \langle \phi_a(\mathbf{k}) | I_\mu^K(\mathbf{k}) | \phi_b(\mathbf{k}) \rangle \langle \phi_b(\mathbf{k}) | I_\nu(\mathbf{k}) | \phi_a(\mathbf{k}) \rangle, \end{aligned} \quad (10)$$

where n_F is the Fermi-Dirac function, and $\{E_a\}$, $\{|\phi_a(\mathbf{k})\rangle\}$ are the eigenvalues and eigenvectors, respectively, of \hat{H}_{BdG} . A key aspect of the expression for Π given by Eq. (10) is that the matrix $I_\nu(\mathbf{k})$, Eq. (6), in Nambu space, has nonzero off diagonal elements $\delta \Delta_m/\delta A_\mu|_0$.

To obtain the expression of $\delta \Delta_m/\delta A_\mu|_0$ we need to calculate the response of Δ to an external vector potential \mathbf{A} . We note that one can treat \mathbf{A} as a parameter in the mean field calculation and use the finite difference approximation to determine $\delta \Delta_m/\delta A_\mu|_0$ (see the SM [76]). This approach requires knowledge of the self-consistent solution for Δ at finite \mathbf{A} as well as $\mathbf{A} = 0$. The linear response expression of $\delta \Delta_m/\delta A_\mu|_0$ requires only the solution at $\mathbf{A} = 0$, and is given by

$$\frac{\delta \Delta_m}{\delta A_\mu} \Big|_0 = \frac{i}{N_c} \lim_{\mathbf{q} \rightarrow 0} \int_0^\infty dt \langle [\hat{\Delta}_m(\mathbf{q}, t), \hat{J}_\mu^p(-\mathbf{q}, 0)] \rangle, \quad (11)$$

where $\hat{\Delta}_m(\mathbf{q}) = U \sum_{\mathbf{k}} c_{m\downarrow}(-\mathbf{k}) c_{m\uparrow}(\mathbf{k}+\mathbf{q})$. Notice that Eq. (11) is equivalent to the inclusion of the anomalous components of the vertex corrections [56,77], the relevant components for the mean-field treatment considered (see

also the discussion on vertex corrections in the SM [76]). The vertex corrections guarantee that the expectation value of the full current operator satisfies the Ward identities, and therefore charge conservation, even when Δ is not homogeneous leading to mixing of responses to transverse and longitudinal vector fields.

Equation (11) leads to a linear equation for $\delta \Delta_m/\delta A_\mu|_0$ of the form

$$\begin{pmatrix} \delta \Delta_\mu^{(R)} \\ \delta \Delta_\mu^{(I)} \end{pmatrix} = \begin{pmatrix} C_\mu^{(R)} \\ C_\mu^{(I)} \end{pmatrix}; \quad K = \begin{pmatrix} K_+^{(R)} & -K_-^{(I)} \\ K_+^{(I)} & K_-^{(R)} \end{pmatrix}, \quad (12)$$

where $\delta \Delta^{(R)}$ and $\delta \Delta^{(I)}$ are the real and imaginary parts of the vector with components $\{\delta \Delta_m/\delta A_\mu|_0\}$, $C_\mu^{(R)}$ and $C_\mu^{(I)}$ are the real and imaginary parts of the vector with components

$$\begin{aligned} (C_\mu)_m = \frac{1}{N_c} \sum_{\mathbf{k},ab} \frac{n_F(E_a(\mathbf{k})) - n_F(E_b(\mathbf{k}))}{E_a(\mathbf{k}) - E_b(\mathbf{k})} \\ \times \langle \phi_a^m(\mathbf{k}) | \tau_- | \phi_b^m(\mathbf{k}) \rangle \langle \phi_b(\mathbf{k}) | I_\mu^K(\mathbf{k}) | \phi_a(\mathbf{k}) \rangle \end{aligned} \quad (13)$$

and $K_\pm^{(R/I)} = \mathcal{A}^{(R/I)} \pm \mathcal{B}^{(R/I)}$ with $\mathcal{A}^{(R/I)}$, $\mathcal{B}^{(R/I)}$ the real/imaginary parts of matrices with elements

$$\begin{aligned} \mathcal{A}_{mm'} = \frac{-1}{N_c} \sum_{\mathbf{k},ab} \frac{n_F(E_a(\mathbf{k})) - n_F(E_b(\mathbf{k}))}{E_a(\mathbf{k}) - E_b(\mathbf{k})} \\ \times \langle \phi_a^m(\mathbf{k}) | \tau_- | \phi_b^m(\mathbf{k}) \rangle \langle \phi_b^{m'}(\mathbf{k}) | \tau_+ | \phi_a^{m'}(\mathbf{k}) \rangle - \frac{1}{U} \delta_{mm'}, \end{aligned} \quad (14)$$

$$\begin{aligned} \mathcal{B}_{mm'} = \frac{-1}{N_c} \sum_{\mathbf{k},ab} \frac{n_F(E_a(\mathbf{k})) - n_F(E_b(\mathbf{k}))}{E_a(\mathbf{k}) - E_b(\mathbf{k})} \\ \times \langle \phi_a^m(\mathbf{k}) | \tau_- | \phi_b^m(\mathbf{k}) \rangle \langle \phi_b^{m'}(\mathbf{k}) | \tau_- | \phi_a^{m'}(\mathbf{k}) \rangle. \end{aligned} \quad (15)$$

In Eqs. (13)–(15), $|\phi_a^m(\mathbf{k})\rangle$ is the component of $|\phi_a(\mathbf{k})\rangle$ on orbital m and the τ 's are Pauli matrices in particle-hole space. Naïvely, $\delta \Delta_m/\delta A_\mu|_0$ can be obtained by inverting Eq. (12). However, the square matrix K is singular, it has rank one less than its dimension. This reflects the fact that the vector Δ_m , and therefore $\delta \Delta_m/\delta A_\mu|_0$, is defined apart from an overall phase α (see the SM [76]). $\delta \Delta_m/\delta A_\mu|_0$, apart from the overall phase α , can be obtained by calculating the pseudoinverse of K via a singular value decomposition (see the SM [76]).

Equations (8), (10), and (12)–(15) allow the calculation of the full superfluid weight. We can write $D_{\mu\nu}^{(s)} = D_{\mu\nu}^{(s0)} + \delta D_{\mu\nu}^s$, where $D_{\mu\nu}^{(s0)}$ is the value of $D_{\mu\nu}^{(s)}$ obtained neglecting the correction due to the response of Δ to \mathbf{A} , and

$$\delta D_{\mu\nu}^s = 2 \operatorname{Re} \left[\sum_m (C_\mu)_m \frac{\delta \Delta_m^*}{\delta A_\nu} \Big|_0 \right] \quad (16)$$

is the correction due to the changes in the pairing potential induced by \mathbf{A} . We note that our result may be obtained using vertex corrections [56,60], which we also discuss in the SM [76]. The correction $\delta D_{\mu\nu}^s$ given by Eq. (16) is gauge invariant (see the SM [76]). To check that the inclusion of the correction $\delta D_{\mu\nu}^s$ returns the accurate quantitative value of $D_{\mu\nu}^{(s)}$, we compare the results obtained by combining Eqs. (8), (10), and (12)–(15), and the ones obtained using the relation $D_{\mu\nu}^{(s)} = (1/V) d^2 F / dA_\mu dA_\nu$. The full derivative of F with respect to \mathbf{A} indicates that also the dependence of F on

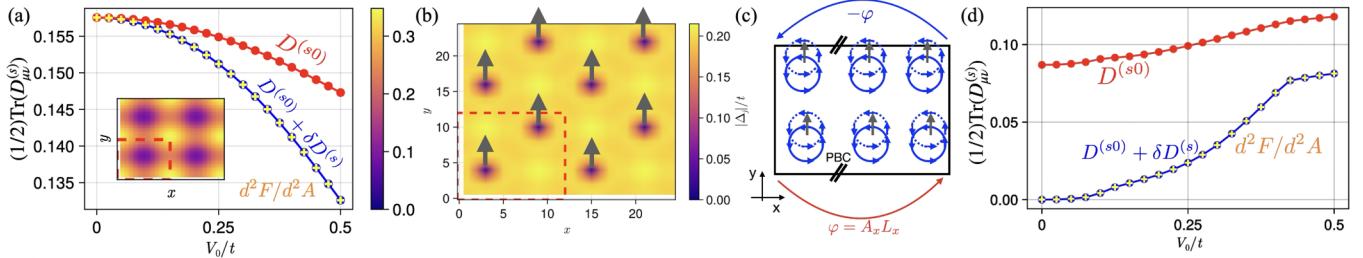


FIG. 1. (a) $(1/2)\text{Tr}(D_{\mu\nu}^{(s)})$ as a function of V_0 without (red points) and with (blue points) the correction from the response of Δ for a 2D superconductor with ten 12×12 unit cells in both the x and y directions ($N_c = 100$), $t = 1$, $\mu = -3.5$, and $U = 3.4$. The yellow crosses show the values obtained by using the second derivative of the free energy. Inset: color plot showing the spatial profile of $|\Delta_j|$ for $V_0 = 0.5$. The dashed red box represents one unit cell. (b) Calculated profile of $|\Delta_j|$ for the case of a superconductor with a vortex lattice induced a magnetic field $B_z = \Phi_0/144a^2$ ($\Phi_0 = h/e$) in the absence of any pinning potential. The gray arrows show the motion of the vortices in response to a constant vector field along the x direction. (c) Schematics showing how the motion of unpinned vortices induces a phase twist, $-\varphi$, that cancels the applied one, $\varphi = A_x L_x$ induced by the vector potential (L_x is the size of the system along the x direction). (d) $(1/2)\text{Tr}(D_{\mu\nu}^{(s)})$ as a function of V_0 without (red points) and with (blue points) the correction from the response of Δ for a 2D superconductor with a vortex lattice as shown in panel (b). As in (a) the yellow crosses show the values obtained by calculating the second derivative of the free energy.

\mathbf{A} through Δ is included. The derivatives $d^2F/dA_\mu dA_\nu$ are calculated numerically for the ground state that is obtained solving self-consistently the gap equation.

Figure 1(a) shows the calculated values of $(1/2)\text{Tr}(D_{\mu\nu}^{(s)})$ for a 2D superconductor on a square lattice with lattice constant $a = 1$ in the presence of the periodic potential

$$V(\mathbf{r}_j) = -\frac{V_0}{2} \left[\cos\left(\frac{2\pi}{M}x_j\right) + \cos\left(\frac{2\pi}{M}y_j\right) \right] \quad (17)$$

with period M . In Eq. (17), $\mathbf{r}_j = (x_j, y_j)$. The potential has the effect of modulating the density of electrons, as well as the amplitude of the order parameter Δ_j , thus rendering the superconductor inhomogeneous; see the inset of Fig. 1(a).

For $V_0 = 0$ the superconductor is homogenous, in this case $(C_\mu)_j = 0$ (see the SM [76]) making $\delta\Delta_m/\delta A_\mu|_0 = 0$ and therefore $D_{\mu\nu}^{(s)} = D_{\mu\nu}^{(s0)}$. The results show that, indeed, for $V_0 = 0$ $D_{\mu\nu}^{(s)}$, shown by the blue circles, coincides with $D_{\mu\nu}^{(s0)}$, shown by the red circles, and with the value obtained by calculating $d^2F/dA_\mu dA_\nu$, yellow crosses. However, for $V_0 \neq 0$, Δ_j is inhomogeneous and so the correction $\delta D_{\mu\nu}^s$ is non-negligible, making $D_{\mu\nu}^{(s)} \neq D_{\mu\nu}^{(s0)}$, as shown in Fig. 1(a). We see that for $V_0 \neq 0$ only the value of $D_{\mu\nu}^{(s)}$ obtained by taking into account the corrections due to $\delta\Delta_m/\delta A_\mu|_0$ agrees with the value of $D_{\mu\nu}^{(s)}$ obtained by calculating $d^2F/dA_\mu dA_\nu$.

The corrections to $D_{\mu\nu}^{(s)}$ due to $\delta\Delta_m/\delta A_\mu|_0$, i.e., $\hat{J}_\mu^{\Delta p}$, become qualitatively very important when vortices are present. A lattice of unpinned vortices was found to have vanishing superfluid weight [53,54]. This can be understood considering that for a vortex lattice in the (x, y) plane induced by a background magnetic field B_z in the direction perpendicular to the plane, for a spatially, perturbing, constant, in-plane, vector potential \mathbf{A} , say along the x direction, the vortices respond by shifting their position along the y direction, as shown in the inset of Fig. 1(b), by an amount $\Delta y = \frac{\hbar}{e} \frac{|\mathbf{A}|}{B_z}$. Because this translation costs no free energy, given that it corresponds to the $\mathbf{q} \rightarrow 0$ Goldstone mode associated to the translational symmetry spontaneously broken by the vortex lattice, we have $D_{\mu\nu}^{(s)} = 0$.

To study the superfluid weight in the presence of vortices, and a pinning periodic potential with period M of the form given by Eq. (17), we consider the case of a 2D superconductor on a square lattice in the presence of a perpendicular background magnetic field B_z [78] (see the SM for details [76]). In Fig. 1(b) we show the results for $D_{\mu\nu}^{(s0)}$, $D_{\mu\nu}^{(s)}$ obtained taking into account the correction $\delta D_{\mu\nu}^s$, and $D_{\mu\nu}^{(s)}$ obtained by taking the second derivative of F with respect to \mathbf{A} . The results show that for $V_0 = 0$, even though an unpinned vortex lattice is present, $D_{\mu\nu}^{(s0)}$ is finite and quite large (red circles in the figure), of the same order as for the case of a superconducting state with no vortices [see Fig. 1(a)]. This contrasts with the expectation that superfluid weight should vanish. The inclusion of the correction $\delta D_{\mu\nu}^s$ leads to $D_{\mu\nu}^{(s)} = 0$ (blue circles), the correct value in the presence of an unpinned vortex lattice, the same value that we find by calculating $D_{\mu\nu}^{(s)}$ as the second derivative of F with respect to \mathbf{A} (yellow crosses). This is one of the key results of the present work: it shows that in the presence of vortices, the correction to $D_{\mu\nu}^{(s)}$ due to the response of Δ_j to \mathbf{A} is essential to obtain the qualitatively correct value of the superfluid weight. As V_0 increases, and the vortices start getting pinned, $D_{\mu\nu}^{(s)}$ also increases from zero and starts getting closer to the value of $D_{\mu\nu}^{(s0)}$. Notice, however, that even for $V_0 = 0.5t$, the value of $D_{\mu\nu}^{(s0)}$ is still about 60% larger than the value given by the full expression of $D_{\mu\nu}^{(s)}$, value that coincides with the one obtained by calculating the second derivative of F with respect to \mathbf{A} .

In summary, we have presented a theoretical approach that, by efficiently taking into account the response of the superconducting order parameter to the external vector potential \mathbf{A} , allows the calculation of the superfluid weight $D_{\mu\nu}^{(s)}$ for strongly inhomogeneous superconductors. Our approach, and results, are directly relevant to the case in which vortices are present in the pairing potential. When the superconducting vortex lattice is not pinned, we find that the response of the superconducting order parameter to \mathbf{A} is essential to obtain the expected result of zero superfluid weight. These results advance the understanding of vortex-superfluid interplay, for example in systems like cuprates and kagome superconductors [79–81], motivating further studies to optimize critical

currents for applications. For two-dimensional systems, the results presented show the importance of the response of the superconducting order parameter to the external vector potential when calculating the critical temperature T_{BKT} for the Berezinskii-Kosterlitz-Thouless phase transition of an inhomogeneous superconductor, given the connection between $D_{\mu\nu}^{(s)}$ and T_{BKT} .

This work was funded by the US Department of Energy, Office of Basic Energy Sciences, via Award

DE-SC0022245. J.S.'s work during the initial phase of the project while at the Pennsylvania State University was funded by the U.S. Department of Energy, Office of Basic Energy Sciences, under Grant No. DE-SC0005042. The authors thank Kukka Huhtinen, Jainendra Jain, Chaoxing Liu, and Valerio Peri for very helpful discussions.

Data availability. The data that support the findings of this article are openly available [82].

[1] D. J. Scalapino, S. R. White, and S. C. Zhang, Superfluid density and the drude weight of the Hubbard model, *Phys. Rev. Lett.* **68**, 2830 (1992).

[2] D. J. Scalapino, S. R. White, and S. Zhang, Insulator, metal, or superconductor: The criteria, *Phys. Rev. B* **47**, 7995 (1993).

[3] V. L. Berezinskii, Destruction of long-range order in one-dimensional and two-dimensional systems having a continuous symmetry group I. Classical systems, *Sov. Phys. JETP* **32**, 493 (1971).

[4] J. M. Kosterlitz and D. J. Thouless, Ordering, metastability and phase transitions in two-dimensional systems, *J. Phys. C* **6**, 1181 (1973).

[5] Y. Cao, V. Fatemi, S. Fang, K. Watanabe, T. Taniguchi, E. Kaxiras, and P. Jarillo-Herrero, Unconventional superconductivity in magic-angle graphene superlattices, *Nature (London)* **556**, 43 (2018).

[6] X. Lu, P. Stepanov, W. Yang, M. Xie, M. A. Aamir, I. Das, C. Urgell, K. Watanabe, T. Taniguchi, G. Zhang, and others, Superconductors, orbital magnets and correlated states in magic-angle bilayer graphene, *Nature (London)* **574**, 653 (2019).

[7] M. Yankowitz, S. Chen, H. Polshyn, Y. Zhang, K. Watanabe, T. Taniguchi, D. Graf, A. F. Young, and C. R. Dean, Tuning superconductivity in twisted bilayer graphene, *Science* **363**, 1059 (2019).

[8] P. Stepanov, I. Das, X. Lu, A. Fahimniya, K. Watanabe, T. Taniguchi, F. H. Koppens, J. Lischner, L. Levitov, and D. K. Efetov, Untying the insulating and superconducting orders in magic-angle graphene, *Nature (London)* **583**, 375 (2020).

[9] Y. Saito, J. Ge, K. Watanabe, T. Taniguchi, and A. F. Young, Independent superconductors and correlated insulators in twisted bilayer graphene, *Nat. Phys.* **16**, 926 (2020).

[10] E. Y. Andrei and A. H. MacDonald, Graphene bilayers with a twist, *Nat. Mater.* **19**, 1265 (2020).

[11] J. M. Park, Y. Cao, K. Watanabe, T. Taniguchi, and P. Jarillo-Herrero, Tunable strongly coupled superconductivity in magic-angle twisted trilayer graphene, *Nature (London)* **590**, 249 (2021).

[12] Z. Hao, A. Zimmerman, P. Ledwith, E. Khalaf, D. H. Najafabadi, K. Watanabe, T. Taniguchi, A. Vishwanath, and P. Kim, Electric field-tunable superconductivity in alternating-twist magic-angle trilayer graphene, *Science* **371**, 1133 (2021).

[13] H. Zhou, T. Xie, T. Taniguchi, K. Watanabe, and A. F. Young, Superconductivity in rhombohedral trilayer graphene, *Nature (London)* **598**, 434 (2021).

[14] Y. Cao, J. M. Park, K. Watanabe, T. Taniguchi, and P. Jarillo-Herrero, Pauli-limit violation and re-entrant superconductivity in moiré graphene, *Nature (London)* **595**, 526 (2021).

[15] H. Zhou, L. Holleis, Y. Saito, L. Cohen, W. Huynh, C. L. Patterson, F. Yang, T. Taniguchi, K. Watanabe, and A. F. Young, Isospin magnetism and spin-polarized superconductivity in Bernal bilayer graphene, *Science* **375**, 774 (2022).

[16] S. Peotta and P. Törmä, Superfluidity in topologically nontrivial flat bands, *Nat. Commun.* **6**, 8944 (2015).

[17] L. Liang, T. I. Vanhala, S. Peotta, T. Siro, A. Harju, and P. Törmä, Band geometry, Berry curvature, and superfluid weight, *Phys. Rev. B* **95**, 024515 (2017).

[18] F. Wu and S. Das Sarma, Quantum geometry and stability of moiré flatband ferromagnetism, *Phys. Rev. B* **102**, 165118 (2020).

[19] B. A. Bernevig, B. Lian, A. Cowsik, F. Xie, N. Regnault, and Z.-D. Song, Twisted bilayer graphene. V. Exact analytic many-body excitations in Coulomb Hamiltonians: Charge gap, Goldstone modes, and absence of Cooper pairing, *Phys. Rev. B* **103**, 205415 (2021).

[20] K.-E. Huhtinen, J. Herzog-Arbeitman, A. Chew, B. A. Bernevig, and P. Törmä, Revisiting flat band superconductivity: Dependence on minimal quantum metric and band touchings, *Phys. Rev. B* **106**, 014518 (2022).

[21] J. Herzog-Arbeitman, V. Peri, F. Schindler, S. D. Huber, and B. A. Bernevig, Superfluid weight bounds from symmetry and quantum geometry in flat bands, *Phys. Rev. Lett.* **128**, 087002 (2022).

[22] A. Lau, S. Peotta, D. Pikulin, E. Rossi, and T. Hyart, Universal suppression of superfluid weight by non-magnetic disorder in *s*-wave superconductors independent of quantum geometry and band dispersion, *SciPost Phys.* **13**, 086 (2022).

[23] P. Törmä, S. Peotta, and B. A. Bernevig, Superconductivity, superfluidity and quantum geometry in twisted multilayer systems, *Nat. Rev. Phys.* **4**, 528 (2022).

[24] P. Törmä, Essay: Where can quantum geometry lead us? *Phys. Rev. Lett.* **131**, 240001 (2023).

[25] A. Bouhon, A. Timmel, and R.-J. Slager, Quantum geometry beyond projective single bands, *arXiv:2303.02180*.

[26] M. Tam and S. Peotta, Geometry-independent superfluid weight in multiorbital lattices from the generalized random phase approximation, *Phys. Rev. Res.* **6**, 013256 (2024).

[27] N. Verma, D. Guerci, and R. Queiroz, Geometric stiffness in interlayer exciton condensates, *Phys. Rev. Lett.* **132**, 236001 (2024).

[28] D. Kaplan, K. P. Lucht, P. A. Volkov, and J. H. Pixley, Quantum geometric photocurrents of quasiparticles in superconductors, [arXiv:2502.12265](https://arxiv.org/abs/2502.12265).

[29] J. Yu, J. Herzog-Arbeitman, and B. A. Bernevig, Universal Wilson loop bound of quantum geometry, *Phys. Rev. Lett.* **135**, 086401 (2025).

[30] G. Jiang, P. Törmä, and Y. Barlas, Superfluid weight cross-over and critical temperature enhancement in singular flat bands, *Proc. Natl. Acad. Sci. USA* **122**, e2416726122 (2025).

[31] R. P. S. Penttilä, K.-E. Huhtinen, and P. Törmä, Flat-band ratio and quantum metric in the superconductivity of modified Lieb lattices, *Commun. Phys.* **8**, 50 (2025).

[32] J. Yu, B. A. Bernevig, R. Queiroz, E. Rossi, P. Törmä, and B.-J. Yang, Quantum geometry in quantum materials, [arXiv:2501.00098](https://arxiv.org/abs/2501.00098).

[33] X. Hu, T. Hyart, D. I. Pikulin, and E. Rossi, Geometric and conventional contribution to the superfluid weight in twisted bilayer graphene, *Phys. Rev. Lett.* **123**, 237002 (2019).

[34] A. Julku, T. J. Peltonen, L. Liang, T. T. Heikkilä, and P. Törmä, Superfluid weight and Berezinskii-Kosterlitz-Thouless transition temperature of twisted bilayer graphene, *Phys. Rev. B* **101**, 060505(R) (2020).

[35] F. Xie, Z. Song, B. Lian, and B. A. Bernevig, Topology-bounded superfluid weight in twisted bilayer graphene, *Phys. Rev. Lett.* **124**, 167002 (2020).

[36] N. Verma, T. Hazra, and M. Randeria, Optical spectral weight, phase stiffness, and T_c bounds for trivial and topological flat band superconductors, *Proc. Natl. Acad. Sci. USA* **118**, e2106744118 (2021).

[37] E. Rossi, Quantum metric and correlated states in two-dimensional systems, *Curr. Opin. Solid State Mater. Sci.* **25**, 100952 (2021).

[38] X. Hu, T. Hyart, D. I. Pikulin, and E. Rossi, Quantum-metric-enabled exciton condensate in double twisted bilayer graphene, *Phys. Rev. B* **105**, L140506 (2022).

[39] I. Mangel, I. Kapon, N. Blau, K. Golubkov, N. Gavish, and A. Keren, Stiffnessometer, a magnetic-field-free superconducting stiffness meter and its application, *Phys. Rev. B* **102**, 024502 (2020).

[40] S. Mallik, G. C. Ménard, G. Saïz, H. Witt, J. Lesueur, A. Gloter, L. Benfatto, M. Bibes, and N. Bergeal, Superfluid stiffness of a KTaO_3 -based two-dimensional electron gas, *Nat. Commun.* **13**, 4625 (2022).

[41] H. Tian, X. Gao, Y. Zhang, S. Che, T. Xu, P. Cheung, K. Watanabe, T. Taniguchi, M. Randeria, F. Zhang, C. N. Lau, and M. W. Bockrath, Evidence for Dirac flat band superconductivity enabled by quantum geometry, *Nature (London)* **614**, 440 (2023).

[42] A. Banerjee, Z. Hao, M. Kreidel, P. Ledwith, I. Phinney, J. M. Park, A. Zimmerman, M. E. Wesson, K. Watanabe, T. Taniguchi *et al.*, Superfluid stiffness of twisted trilayer graphene superconductors, *Nature (London)* **638**, 93 (2025).

[43] M. Tanaka, J. Î.-j. Wang, T. H. Dinh, D. Rodan-Legrain, S. Zaman, M. Hays, A. Almanaky, B. Kannan, D. K. Kim, B. M. Niedzielski, K. Serniak, M. E. Schwartz, K. Watanabe, T. Taniguchi, T. P. Orlando, S. Gustavsson, J. A. Grover, P. Jarillo-Herrero, and W. D. Oliver, Superfluid stiffness of magic-angle twisted bilayer graphene, *Nature (London)* **638**, 99 (2025).

[44] A. Ghosal, M. Randeria, and N. Trivedi, Role of spatial amplitude fluctuations in highly disordered s -wave superconductors, *Phys. Rev. Lett.* **81**, 3940 (1998).

[45] A. Paramekanti, N. Trivedi, and M. Randeria, Upper bounds on the superfluid stiffness of disordered systems, *Phys. Rev. B* **57**, 11639 (1998).

[46] A. Ghosal, M. Randeria, and N. Trivedi, Inhomogeneous pairing in highly disordered s -wave superconductors, *Phys. Rev. B* **65**, 014501 (2001).

[47] A. Datta, A. Banerjee, N. Trivedi, and A. Ghosal, Insulating vortex cores in disordered superconductors, *Phys. Rev. B* **107**, L140502 (2023).

[48] A. V. Khvalyuk, T. Charpentier, N. Roch, B. Sacépé, and M. V. Feigel'man, Near power-law temperature dependence of the superfluid stiffness in strongly disordered superconductors, *Phys. Rev. B* **109**, 144501 (2024).

[49] A. Uri, S. Grover, Y. Cao, J. A. Crosse, K. Bagani, D. Rodan-Legrain, Y. Myasoedov, K. Watanabe, T. Taniguchi, P. Moon, M. Koshino, P. Jarillo-Herrero, and E. Zeldov, Mapping the twist-angle disorder and Landau levels in magic-angle graphene, *Nature (London)* **581**, 47 (2020).

[50] Y. Cao, D. Rodan-Legrain, J. M. Park, N. F. Q. Yuan, K. Watanabe, T. Taniguchi, R. M. Fernandes, L. Fu, and P. Jarillo-Herrero, Nematicity and competing orders in superconducting magic-angle graphene, *Science* **372**, 264 (2021).

[51] D. Cho, K. Bastiaans, D. Chatzopoulos, G. Gu, and M. Allan, A strongly inhomogeneous superfluid in an iron-based superconductor, *Nature (London)* **571**, 541 (2019).

[52] Y. Iguchi, J. A. Straquadi, C. Murthy, S. A. Kivelson, A. G. Singh, I. R. Fisher, and K. A. Moler, Anomalous superfluid density in a disordered charge-density-wave material: Pd-intercalated ErTe_3 , *Phys. Rev. Lett.* **133**, 036001 (2024).

[53] S. Teitel and C. Jayaprakash, Phase transitions in frustrated two-dimensional XY models, *Phys. Rev. B* **27**, 598 (1983).

[54] M. Franz and S. Teitel, Vortex-lattice melting in two-dimensional superconducting networks and films, *Phys. Rev. B* **51**, 6551 (1995).

[55] G. Seibold, L. Benfatto, C. Castellani, and J. Lorenzana, Superfluid density and phase relaxation in superconductors with strong disorder, *Phys. Rev. Lett.* **108**, 207004 (2012).

[56] J. R. Schrieffer, *Theory of Superconductivity*, revised printing ed., Advanced Book Classics (CRC Press, Boca Raton, London, New York, 1964).

[57] P. W. Anderson, Random-phase approximation in the theory of superconductivity, *Phys. Rev.* **112**, 1900 (1958).

[58] P. W. Anderson, Coherent excited states in the theory of superconductivity: Gauge invariance and the Meissner effect, *Phys. Rev.* **110**, 827 (1958).

[59] G. Rickayzen, Collective excitations in the theory of superconductivity, *Phys. Rev.* **115**, 795 (1959).

[60] Y. Nambu, Quasi-particles and gauge invariance in the theory of superconductivity, *Phys. Rev.* **117**, 648 (1960).

[61] L. P. Kadanoff and P. C. Martin, Theory of many-particle systems. II. Superconductivity, *Phys. Rev.* **124**, 670 (1961).

[62] I. Kulik, O. Entin-Wohlman, and R. Orbach, Pair susceptibility and mode propagation in superconductors: A microscopic approach, *J. Low Temp. Phys.* **43**, 591 (1981).

[63] V. J. Emery and S. A. Kivelson, Importance of phase fluctuations in superconductors with small superfluid density, *Nature (London)* **374**, 434 (1995).

[64] Y. Zha, K. Levin, and D. Z. Liu, Collective modes and implications for c -axis optical experiments in layered cuprates, *Phys. Rev. B* **51**, 6602 (1995).

[65] P. I. Arseev, S. O. Loiko, and N. K. Fedorov, Theory of gauge-invariant response of superconductors to an external electromagnetic field, *Phys. Usp.* **49**, 1 (2006).

[66] K. Wang, R. Boyack, and K. Levin, Higgs amplitude mode in optical conductivity in the presence of a supercurrent: Gauge-invariant formulation with disorder, *Phys. Rev. B* **111**, 144512 (2025).

[67] H. Guo, C.-C. Chien, and Y. He, Theories of linear response in BCS superfluids and how they meet fundamental constraints, *J. Low Temp. Phys.* **172**, 5 (2013).

[68] S. Yin, J. P. Martikainen, and P. Törmä, Fulde-Ferrell states and Berezinskii-Kosterlitz-Thouless phase transition in two-dimensional imbalanced Fermi gases, *Phys. Rev. B* **89**, 014507 (2014).

[69] R. Boyack, B. M. Anderson, C.-T. Wu, and K. Levin, Gauge-invariant theories of linear response for strongly correlated superconductors, *Phys. Rev. B* **94**, 094508 (2016).

[70] R. Boyack, C.-T. Wu, B. M. Anderson, and K. Levin, Collective mode contributions to the Meissner effect: Fulde-Ferrell and pair-density wave superfluids, *Phys. Rev. B* **95**, 214501 (2017).

[71] S. Peotta, Superconductivity, generalized random phase approximation and linear scaling methods, *New J. Phys.* **24**, 113019 (2022).

[72] S. M. Chan, B. Grémaud, and G. G. Batrouni, Pairing and superconductivity in quasi-one-dimensional flat-band systems: Creutz and Sawtooth lattices, *Phys. Rev. B* **105**, 024502 (2022).

[73] G. Jiang and Y. Barlas, Geometric superfluid weight of composite bands in multiorbital superconductors, *Phys. Rev. B* **109**, 214518 (2024).

[74] N. Nunchot and Y. Yanase, Nonlinear diode effect and Berezinskii-Kosterlitz-Thouless transition in purely two-dimensional noncentrosymmetric superconductors, *Phys. Rev. B* **111**, 094515 (2025).

[75] S. Teitel, The two-dimensional fully frustrated XY model, in *40 Years of Berezinskii-Kosterlitz-Thouless Theory* (World Scientific Press, Singapore, 2013), pp. 201–235.

[76] See Supplemental Material at <http://link.aps.org/supplemental/10.1103/9gc8-q16z> for details on vertex corrections, finite difference methods, inversion of the singular matrix, and additional results including figures on energy vs twist and average pairing potential.

[77] Z. M. Raines, S.-S. Zhang, and A. V. Chubukov, Superfluid stiffness within Eliashberg theory: The role of vertex corrections, *Phys. Rev. B* **109**, 144505 (2024).

[78] J. Schirmer, J. K. Jain, and C.-X. Liu, Topological superconductivity induced by spin-orbit coupling, perpendicular magnetic field, and superlattice potential, *Phys. Rev. B* **109**, 134518 (2024).

[79] J. T. Zhang, J. Kim, M. Huefner, C. Ye, S. Kim, P. C. Canfield, R. Prozorov, O. M. Auslaender, and J. E. Hoffman, Single-vortex pinning and penetration depth in superconducting $\text{NdFeAsO}_{1-x}\text{F}_x$, *Phys. Rev. B* **92**, 134509 (2015).

[80] S. Hu, J. Qiao, G. Gu, Q.-K. Xue, and D. Zhang, Vortex entropy and superconducting fluctuations in ultrathin underdoped $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+x}$ superconductor, *Nat. Commun.* **15** (2024).

[81] Y. Xie, N. Chalus, Z. Wang, W. Yao, J. Liu, Y. Yao, J. S. White, L. M. DeBeer-Schmitt, J.-X. Yin, P. Dai, and M. R. Eskildsen, Conventional superconductivity in the doped kagome superconductor $\text{Cs}(\text{V}_{0.86}\text{Ta}_{0.14})_3\text{Sb}_5$ from vortex lattice studies, *Nat. Commun.* **15** (2024).

[82] J. Schirmer, Data for “Superfluid weight of strongly inhomogeneous superconductors” [Data set], Zenodo (2025), <https://doi.org/10.5281/zenodo.15730586>.

Supplementary Materials for “Superfluid Weight of Strongly Inhomogeneous Superconductors”

Jonathan Schirmer^{1,2} and Enrico Rossi¹

¹*Department of Physics, William & Mary, Williamsburg, Virginia 23187, USA*

²*Department of Physics, 104 Davey Lab, The Pennsylvania State University, University Park, Pennsylvania 16802, USA*

Contents

Hamiltonian	1
Current Operator	2
Paramagnetic Current	4
Diamagnetic Current	6
Superfluid Weight	6
Paramagnetic Current-Current Correlation Function	6
Calculating the Response of Δ	7
Correction to the Superfluid Weight	9
Example: Uniform Superconductor	10
Relation to Vertex Corrections	10
Gauge Invariance	10
Inversion of Equation (12)	13
Superconductor with vortex lattice	13
References	13

Hamiltonian

Let us suppose our system is defined on a lattice with sites $\{\mathbf{r}_j\}$, where the site/orbital labels are j , and with bonds described by a set of vectors $\{\beta_j^\ell\}$ that start at site j , are labelled at each j by the label ℓ , and where $\text{Arg}(\beta_j^\ell) \in (-\pi/2, \pi/2]$ in 2D. The latter condition is so that we consider “forward hopping” only. We take care of backward hopping, at the same time as ensuring Hermiticity, by adding the Hermitian conjugate of the forward hopping terms to the Hamiltonian. If two orbitals reside in the same location, one can unambiguously define β_j^ℓ via point-splitting. We include an on-site superconducting pairing, originating from an on-site attractive interaction of magnitude $U > 0$. The mean field Hamiltonian is

$$\hat{H}_{\text{MF}} = - \sum_{j, \ell, \sigma} \left(t_j^\ell c_{j+\beta_j^\ell, \sigma}^\dagger c_{j, \sigma} + \text{H.c.} \right) - \sum_{j, \sigma} (\mu - V_j) c_{j, \sigma}^\dagger c_{j, \sigma} - \sum_j \left(\Delta_j c_{j, \uparrow}^\dagger c_{j, \downarrow}^\dagger + \Delta_j^* c_{j, \downarrow} c_{j, \uparrow} - \frac{|\Delta_j|^2}{U} \right) \quad (1)$$

where the subscript j is shorthand for the position vector \mathbf{r}_j , the complex hopping amplitude along bond β_j^ℓ is t_j^ℓ , the chemical potential is μ , V_j is an applied potential, and, at zero temperature, $\Delta_j = U \langle c_{j, \downarrow} c_{j, \uparrow} \rangle$ with the angle bracket denoting equilibrium expectation values at temperature T . These are the self-consistency equations.

Suppose that the system possesses a translational invariance by vectors $\mathbf{a}_1, \mathbf{a}_2$ (specializing for 2D here). We may then define unit cells whose locations we specify by $\mathbf{R}_i = m\mathbf{a}_1 + n\mathbf{a}_2$ with $m, n \in \mathbb{Z}$. The position of any orbital can then be given by

$$\mathbf{r}_j = \mathbf{R}_i + \mathbf{b}_m \quad (2)$$

where \mathbf{b}_m specifies the location of the orbital *within the unit cell*. The bonds and the hopping amplitudes then possess this translational invariance:

$$\beta_{j+\mathbf{R}}^\ell = \beta_j^\ell \quad (3)$$

$$t_{j+\mathbf{R}}^\ell = t_j^\ell \quad (4)$$

where the subscript $j + \mathbf{R}$ is shorthand for $\mathbf{r}_j + \mathbf{R}_i$. We will also suppose that the solution to the self-consistency equations possesses this same periodicity:

$$\Delta_{j+\mathbf{R}} = \Delta_j \quad (5)$$

We thus perform the Fourier transformation

$$c_{j\sigma} = \frac{1}{\sqrt{N_c}} \sum_{\mathbf{k}} c_{m,\sigma}(\mathbf{k}) e^{i\mathbf{k}\cdot\mathbf{r}_j} \quad (6)$$

where m is shorthand for $\tilde{\mathbf{r}}_j$. Using the basis of Nambu spinors

$$\hat{\Psi}(\mathbf{k}) = \begin{pmatrix} c_{1,\uparrow}(\mathbf{k}) \\ \vdots \\ c_{N,\uparrow}(\mathbf{k}) \\ c_{1,\downarrow}^\dagger(-\mathbf{k}) \\ \vdots \\ c_{N,\downarrow}^\dagger(-\mathbf{k}) \end{pmatrix} \quad (7)$$

with N the number of sites/orbitals per unit cell, the Hamiltonian (1) can then be cast in Bogoliubov-de Gennes (BdG) form:

$$\hat{\mathcal{H}}_{\text{MF}} = \sum_{\mathbf{k}} \hat{\Psi}^\dagger(\mathbf{k}) H_{\text{BdG}}(\mathbf{k}) \hat{\Psi}(\mathbf{k}) + \sum_{\mathbf{k}} \text{Tr}[H(\mathbf{k})] + \frac{|\Delta_j|^2}{U} \quad (8)$$

where

$$H_{\text{BdG}}(\mathbf{k}) = \begin{pmatrix} H(\mathbf{k}) & -\Delta \\ -\Delta^* & -H^*(-\mathbf{k}) \end{pmatrix} \quad (9)$$

is the BdG Hamiltonian, $H(\mathbf{k})$ is the normal state Hamiltonian, and

$$\Delta = \begin{pmatrix} \Delta_1 & 0 & 0 & \cdots & 0 \\ 0 & \Delta_2 & 0 & \cdots & 0 \\ 0 & 0 & \Delta_3 & \cdots & 0 \\ \vdots & \vdots & \vdots & \ddots & \vdots \\ 0 & 0 & 0 & \cdots & \Delta_N \end{pmatrix} \quad (10)$$

Current Operator

In this Supplementary Materials, \mathbf{A} will refer to a probe electromagnetic potential. The orbital effect of any background magnetic field is accommodated in the model by the complex hopping amplitudes t_j^ℓ . To determine the current, we must specify how the system couples to an external vector potential $\mathbf{A}(\mathbf{r}, t)$. We suppose the hopping part of the Hamiltonian couples via a Peierls substitution

$$t_j^\ell \rightarrow \exp(i\phi_j^\ell) t_j^\ell \quad (11)$$

where

$$\phi_j^\ell = \int_{\mathbf{r}_j}^{\mathbf{r}_j + \beta_j^\ell} \mathbf{A}(\mathbf{r}, t) \cdot d\mathbf{r} \quad (12)$$

Notice that this change in the hopping amplitudes leads to a change in the groundstate $|G\rangle$ which in general leads to a change in Δ_j . We will compute this change in later sections. We choose the path of integration to be the straight line connecting \mathbf{r}_j to $\mathbf{r}_j + \beta_j^\ell$ given by the vector β_j^ℓ .

The system only couples to the average value of $\mathbf{A}(\mathbf{r}, t)$ along the bonds. This is because

$$\int_{\mathbf{r}_j}^{\mathbf{r}_j + \beta_j^\ell} \mathbf{A}(\mathbf{r}, t) \cdot d\mathbf{r} = \mathbf{A}_j^\ell(t) \cdot \beta_j^\ell \quad (13)$$

where $\mathbf{A}_j^\ell(t)$ denotes the average value of $\mathbf{A}(\mathbf{r}, t)$ along bond β_j^ℓ . The current along bond β_j^ℓ (the current in lattice models is defined on the bonds) is given by

$$\hat{\mathbf{J}}_j^\ell = -\frac{\delta \hat{\mathcal{H}}_{\text{MF}}}{\delta \mathbf{A}_j^\ell} = \sum_{\sigma} \left(i\beta_j^\ell t_j^\ell e^{i\phi_j^\ell} c_{j+\beta_j^\ell, \sigma}^\dagger c_{j, \sigma} + \text{H.c.} \right) + \sum_i \left(\frac{\delta \Delta_i}{\delta \mathbf{A}_j^\ell} c_{i, \uparrow}^\dagger c_{i, \downarrow}^\dagger + \frac{\delta \Delta_i^*}{\delta \mathbf{A}_j^\ell} c_{i, \downarrow} c_{i, \uparrow} - \frac{1}{U} \frac{\delta |\Delta_i|^2}{\delta \mathbf{A}_j^\ell} \right) \quad (14)$$

$$= \beta_j^\ell \sum_{\sigma} \left(i t_j^\ell e^{i\phi_j^\ell} c_{j+\beta_j^\ell, \sigma}^\dagger c_{j, \sigma} + \text{H.c.} \right) + \beta_j^\ell \sum_i \left(\frac{\delta \Delta_i}{\delta \phi_j^\ell} c_{i, \uparrow}^\dagger c_{i, \downarrow}^\dagger + \frac{\delta \Delta_i^*}{\delta \phi_j^\ell} c_{i, \downarrow} c_{i, \uparrow} - \frac{1}{U} \frac{\delta |\Delta_i|^2}{\delta \phi_j^\ell} \right) \quad (15)$$

$$\equiv \hat{\mathbf{J}}_j^{\ell K} + \hat{\mathbf{J}}_j^{\ell \Delta} \quad (16)$$

The first sum in (15) is denoted $\hat{\mathbf{J}}_j^{\ell K}$ and is the contribution of the current coming from the kinetic energy. The second sum, which is the contribution of the current from the pairing potential, is denoted $\hat{\mathbf{J}}_j^{\ell \Delta}$. The distinction between these two contributions, which we may call *kinetic current* and *pairing current*, respectively, will play an important role in this SM. We see explicitly that the current is directed along the bonds. We have also taken the chemical potential to be fixed.

We make a few additional comments on (15):

1. In general, $\delta \Delta_j / \delta \phi_{j'}^\ell \neq 0$ for $j \neq j'$. For example, when varying ϕ_j^ℓ , we should at the very least expect the pairing potential Δ_i to respond at the starting and ending sites of the bond β_j^ℓ .
2. The self-consistency equations imply that the average pairing current vanishes $\langle \hat{\mathbf{J}}_j^{\ell \Delta} \rangle \equiv 0$. Thus the average current is given by the average kinetic current

$$\langle \hat{\mathbf{J}}_j^\ell \rangle = \beta_j^\ell \sum_{\sigma} \left(i t_j^\ell e^{i\phi_j^\ell} \langle c_{j+\beta_j^\ell, \sigma}^\dagger c_{j, \sigma} \rangle + \text{c.c.} \right) = \langle \hat{\mathbf{J}}_j^{\ell K} \rangle \quad (17)$$

However, the pairing current does contribute to current correlations in the system, as we shall see.

If we are only interested in the responses of the system to vector potentials which vary slowly in space compared to the length of the bonds, we may replace $\mathbf{A}_j^\ell \rightarrow \mathbf{A}(\mathbf{r}_j, t)$, up to negligible error of $\mathcal{O}(|\beta_j^\ell|/\lambda)$, where λ is the characteristic length scale of variations in $\mathbf{A}(\mathbf{r}, t)$. We can then meaningfully define the current at the lattice sites by

$$\begin{aligned} \hat{J}_\mu(\mathbf{r}_j) &= -\frac{\delta \hat{\mathcal{H}}_{\text{MF}}}{\delta A_\mu(\mathbf{r}_j)} = \sum_{\ell, \sigma} \left(i(\beta_j^\ell)_\mu t_j^\ell e^{i\mathbf{A}(\mathbf{r}_j, t) \cdot \beta_j^\ell} c_{j+\beta_j^\ell, \sigma}^\dagger c_{j, \sigma} + \text{H.c.} \right) \\ &\quad + \sum_{j'} \left(\frac{\delta \Delta_{j'}}{\delta A_\mu(\mathbf{r}_j)} c_{i, \uparrow}^\dagger c_{i, \downarrow}^\dagger + \frac{\delta \Delta_{j'}^*}{\delta A_\mu(\mathbf{r}_j)} c_{i, \downarrow} c_{i, \uparrow} - \frac{1}{U} \frac{\delta |\Delta_{j'}|^2}{\delta A_\mu(\mathbf{r}_j)} \right) \\ &\equiv \hat{J}_\mu^K(\mathbf{r}_j) + \hat{J}_\mu^\Delta(\mathbf{r}_j) \end{aligned} \quad (18)$$

If the system is perturbed by a vector potential of the form $A_\mu(\mathbf{r}, t) = A_\mu(\mathbf{q}, t) e^{-i\mathbf{q} \cdot \mathbf{r}}$ then the corresponding coupling is

$$\sum_{j, \mu} \frac{\delta \hat{\mathcal{H}}_{\text{MF}}}{\delta A_\mu(\mathbf{r}_j, t)} A_\mu(\mathbf{q}, t) e^{-i\mathbf{q} \cdot \mathbf{r}_j} = - \sum_{\mu} A_\mu(\mathbf{q}, t) \sum_j \hat{J}_\mu(\mathbf{r}_j, t) e^{-i\mathbf{q} \cdot \mathbf{r}_j} = - \sum_{\mu} A_\mu(\mathbf{q}, t) \hat{J}_\mu(\mathbf{q}, t) \quad (19)$$

where μ is a spatial index ($\mu = x, y, \dots$). Thus

$$\begin{aligned}\hat{J}_\mu(\mathbf{q}) &= \sum_{j,\ell,\sigma} \left(i(\beta_j^\ell)_\mu t_j^\ell e^{i\mathbf{A}(\mathbf{r}_j,t) \cdot \beta_j^\ell} c_{j+\beta_j^\ell,\sigma}^\dagger c_{j,\sigma} + \text{H.c.} \right) e^{-i\mathbf{q} \cdot \mathbf{r}_j} \\ &+ \sum_{j,j'} \left(\frac{\delta\Delta_{j'}}{\delta A_\mu(\mathbf{r}_j)} c_{i,\uparrow}^\dagger c_{i,\downarrow}^\dagger + \frac{\delta\Delta_{j'}^*}{\delta A_\mu(\mathbf{r}_j)} c_{i,\downarrow} c_{i,\uparrow} - \frac{1}{U} \frac{\delta|\Delta_{j'}|^2}{\delta A_\mu(\mathbf{r}_j)} \right) e^{-i\mathbf{q} \cdot \mathbf{r}_j} \\ &\equiv \hat{J}_\mu^K(\mathbf{q}) + \hat{J}_\mu^\Delta(\mathbf{q})\end{aligned}\quad (20)$$

Paramagnetic Current

It is useful to decompose the current into paramagnetic and diamagnetic components

$$\hat{J}_\mu(\mathbf{q}) = \hat{J}_\mu^p(\mathbf{q}) + \hat{T}_{\mu\nu}(\mathbf{q}) A_\nu(\mathbf{q}) \quad (21)$$

where there is an implied sum over ν . Both $\hat{J}_\mu^p(\mathbf{q})$ and $\hat{T}_{\mu\nu}(\mathbf{q})$ admit further decomposition into kinetic and pairing contributions, as in the previous section. The kinetic component of the paramagnetic current is

$$\hat{J}_\mu^{K,p}(\mathbf{q}) = \sum_{j,\ell,\sigma} \left(i(\beta_j^\ell)_\mu t_j^\ell c_{j+\beta_j^\ell,\sigma}^\dagger c_{j,\sigma} - i(\beta_j^\ell)_\mu t_j^{\ell*} c_{j,\sigma}^\dagger c_{j+\beta_j^\ell,\sigma} \right) e^{-i\mathbf{q} \cdot \mathbf{r}_j} \quad (22)$$

$$= \frac{i}{N_c} \sum_{m,\ell,\sigma} \sum_{\mathbf{k}} \left(\beta_m^\ell \right)_\mu \left[t_m^\ell e^{-i\mathbf{k} \cdot \beta_m^\ell} c_{m+\beta_m^\ell,\sigma}^\dagger(\mathbf{k}) c_{m\sigma}(\mathbf{k} + \mathbf{q}) - t_m^{\ell*} e^{i(\mathbf{k} + \mathbf{q}) \cdot \beta_m^\ell} c_{m\sigma}^\dagger(\mathbf{k}) c_{m+\beta_m^\ell,\sigma}(\mathbf{k} + \mathbf{q}) \right] \quad (23)$$

where we have used (6).

The pairing contribution to the paramagnetic current is

$$\begin{aligned}\hat{J}_\mu^\Delta(\mathbf{q}) &= \sum_{j'} \left[\left(\sum_j \frac{\delta\Delta_{j'}}{\delta A_\mu(\mathbf{r}_j)} \Big|_{A=0} e^{-i\mathbf{q} \cdot \mathbf{r}_j} \right) c_{j',\uparrow}^\dagger c_{j',\downarrow}^\dagger + \left(\sum_j \frac{\delta\Delta_{j'}^*}{\delta A_\mu(\mathbf{r}_j)} \Big|_{A=0} e^{-i\mathbf{q} \cdot \mathbf{r}_j} \right) c_{j',\downarrow} c_{j',\uparrow} - \left(\sum_j \frac{1}{U} \frac{\delta|\Delta_{j'}|^2}{\delta A_\mu(\mathbf{r}_j)} \Big|_{A=0} e^{-i\mathbf{q} \cdot \mathbf{r}_j} \right) \right] \\ &= \sum_{j'} \left[\frac{\delta\Delta_{j'}}{\delta A_\mu(\mathbf{q})} \Big|_{A=0} c_{j',\uparrow}^\dagger c_{j',\downarrow}^\dagger + \frac{\delta\Delta_{j'}^*}{\delta A_\mu(\mathbf{q})} \Big|_{A=0} c_{j',\downarrow} c_{j',\uparrow} - \frac{1}{U} \frac{\delta|\Delta_{j'}|^2}{\delta A_\mu(\mathbf{q})} \Big|_{A=0} \right]\end{aligned}\quad (24)$$

where the derivatives with respect to \mathbf{A} are evaluated at $\mathbf{A} = 0$. Hereafter, all derivatives with respect to \mathbf{A} will be evaluated at $\mathbf{A} = 0$; thus, we omit the evaluation symbol on the derivatives from now on. We have used that the variation $\delta\Delta_{j'}$ with respect to a vector potential of the form $\delta A_\mu(\mathbf{r}, t) = \delta A_\mu(\mathbf{q}, t) e^{-i\mathbf{q} \cdot \mathbf{r}}$ is

$$\delta\Delta_{j'} = \sum_{j'} \frac{\delta\Delta_{j'}}{\delta A_\mu(\mathbf{r}_j)} \delta A_\mu(\mathbf{q}, t) e^{-i\mathbf{q} \cdot \mathbf{r}_j} \quad (25)$$

so that

$$\sum_j \frac{\delta\Delta_{j'}}{\delta A_\mu(\mathbf{r}_j)} e^{-i\mathbf{q} \cdot \mathbf{r}_j} = \frac{\delta\Delta_{j'}}{\delta A_\mu(\mathbf{q})} \quad (26)$$

Recall that we have assumed that Δ_j at $\mathbf{A} = 0$ is periodic with the same periodicity as the hopping amplitudes t_j^ℓ , i.e. we can still define a unit cell by the vectors $\mathbf{a}_1, \mathbf{a}_2$ (in 2D) in the presence of pairing. More generally we take Δ_i to be periodic, and take its period to be commensurate with that of the hopping amplitudes. This situation requires a modification of $\mathbf{a}_1, \mathbf{a}_2$, but otherwise no generality is lost. Thus Δ_j is only a function of the intra-unit cell label. In other words,

$$\Delta_j = \Delta_m \quad (27)$$

From this, it follows that $\frac{\delta\Delta_{j'}}{\delta A_\mu(\mathbf{q})}$ can be written as a periodic function times a plane wave:

$$\frac{\delta\Delta_{j'}}{\delta A_\mu(\mathbf{q})} = \frac{\delta\Delta_m}{\delta A_\mu(\mathbf{q})} e^{-i\mathbf{q}\cdot\mathbf{R}_i} \quad (28)$$

Thus the pairing contribution to the current, after using (6), is

$$\hat{J}_\mu^{\Delta,p}(\mathbf{q}) = \frac{1}{N_c} \sum_{m,\mathbf{k}} \left[\frac{\delta\Delta_m}{\delta A_\mu(\mathbf{q})} c_{m,\uparrow}^\dagger(\mathbf{k}) c_{m,\downarrow}^\dagger(-\mathbf{k} - \mathbf{q}) + \frac{\delta\Delta_m^*}{\delta A_\mu(\mathbf{q})} c_{m,\downarrow}(-\mathbf{k}) c_{m,\uparrow}(\mathbf{k} + \mathbf{q}) \right] - \sum_j \frac{1}{U} \frac{\delta|\Delta_j|^2}{\delta A_\mu(\mathbf{q})} \quad (29)$$

The paramagnetic current is then

$$\begin{aligned} \hat{J}_\mu^p(\mathbf{q}) = & \frac{i}{N_c} \sum_{m,\ell,\sigma} \sum_{\mathbf{k}} (\beta_m^\ell)_\mu \left[t_m^\ell e^{-i\mathbf{k}\cdot\beta_m^\ell} c_{m+\beta_m^\ell\sigma}^\dagger(\mathbf{k}) c_{m\sigma}(\mathbf{k} + \mathbf{q}) - t_m^{\ell*} e^{i(\mathbf{k}+\mathbf{q})\cdot\beta_m^\ell} c_{m\sigma}^\dagger(\mathbf{k}) c_{m+\beta_m^\ell\sigma}(\mathbf{k} + \mathbf{q}) \right] \\ & + \frac{1}{N_c} \sum_{m,\mathbf{k}} \left[\frac{\delta\Delta_m}{\delta A_\mu(\mathbf{q})} c_{m,\uparrow}^\dagger(\mathbf{k}) c_{m,\downarrow}^\dagger(-\mathbf{k} - \mathbf{q}) + \frac{\delta\Delta_m^*}{\delta A_\mu(\mathbf{q})} c_{m,\downarrow}(-\mathbf{k}) c_{m,\uparrow}(\mathbf{k} + \mathbf{q}) \right] - \sum_i \frac{1}{U} \frac{\delta|\Delta_i|^2}{\delta A_\mu(\mathbf{q})} \end{aligned} \quad (30)$$

It is convenient to write the kinetic part of the current operator in the following way (what follows is merely a matter of convenient notation)

$$\begin{aligned} \hat{J}_\mu^{K,p}(\mathbf{q}) = & \frac{1}{N_c} \sum_{\mathbf{k},\sigma} \sum_{mm'} J_{mm';\mu}(\mathbf{k},\mathbf{q}) c_{m\sigma}^\dagger(\mathbf{k}) c_{m'\sigma}(\mathbf{k} + \mathbf{q}) \\ = & \frac{1}{N_c} \sum_{\mathbf{k}} \sum_{mm'} \left[J_{mm';\mu}(\mathbf{k},\mathbf{q}) c_{m\uparrow}^\dagger(\mathbf{k}) c_{m'\uparrow}(\mathbf{k} + \mathbf{q}) - J_{m'm;\mu}(-\mathbf{k} - \mathbf{q},\mathbf{q}) c_{m\downarrow}(-\mathbf{k}) c_{m'\downarrow}^\dagger(-\mathbf{k} - \mathbf{q}) \right] + \text{c-numbers} \end{aligned} \quad (31)$$

where m and m' are site/orbital labels. The matrix elements $J_{mm';\mu}(\mathbf{k},\mathbf{q})$ can be read off from (30). Now, Hermiticity of the current operator implies $J_{m'm;\mu}(-\mathbf{k} - \mathbf{q},\mathbf{q}) = J_{mm';\mu}(-\mathbf{k},-\mathbf{q})^*$. Thus the total paramagnetic current can be written in the basis

$$\psi_m(\mathbf{k}) = \begin{pmatrix} c_{m\uparrow}(\mathbf{k}) \\ c_{m\downarrow}^\dagger(-\mathbf{k}) \end{pmatrix}$$

as

$$\begin{aligned} \hat{J}_\mu^p(\mathbf{q}) = & \frac{1}{N_c} \sum_{\mathbf{k}} \sum_{mm'} \psi_m^\dagger(\mathbf{k}) \begin{pmatrix} J_{mm';\mu}(\mathbf{k},\mathbf{q}) & \frac{\delta\Delta_m}{\delta A_\mu(\mathbf{q})} \delta_{mm'} \\ \frac{\delta\Delta_m^*}{\delta A_\mu(\mathbf{q})} \delta_{mm'} & -J_{mm';\mu}^*(-\mathbf{k},-\mathbf{q}) \end{pmatrix} \psi_{m'}(\mathbf{k} + \mathbf{q}) + \text{c-numbers} \\ \equiv & \frac{1}{N_c} \sum_{\mathbf{k}} \sum_{mm'} \psi_m^\dagger(\mathbf{k}) I_{mm';\mu}(\mathbf{k},\mathbf{q}) \psi_{m'}(\mathbf{k} + \mathbf{q}) + \text{c-numbers} \end{aligned} \quad (32)$$

where

$$I_{mm';\mu}(\mathbf{k},\mathbf{q}) = \begin{pmatrix} J_{mm';\mu}(\mathbf{k},\mathbf{q}) & \frac{\delta\Delta_m}{\delta A_\mu(\mathbf{q})} \delta_{mm'} \\ \frac{\delta\Delta_m^*}{\delta A_\mu(\mathbf{q})} \delta_{mm'} & -J_{mm';\mu}^*(-\mathbf{k},-\mathbf{q}) \end{pmatrix} \quad (33)$$

It is convenient to do the same for the kinetic current only:

$$\hat{J}_\mu^{K,p}(\mathbf{q}) = \frac{1}{N_c} \sum_{\mathbf{k}} \sum_{mm'} \psi_m^\dagger(\mathbf{k}) I_{mm';\mu}^K(\mathbf{k},\mathbf{q}) \psi_m'(\mathbf{k} + \mathbf{q}) + \text{c-numbers} \quad (34)$$

where

$$I_{mm';\mu}^K(\mathbf{k},\mathbf{q}) = \begin{pmatrix} J_{mm';\mu}(\mathbf{k},\mathbf{q}) & 0 \\ 0 & -J_{mm';\mu}^*(-\mathbf{k},-\mathbf{q}) \end{pmatrix} \quad (35)$$

Diamagnetic Current

The diamagnetic current should also be computed in order to calculate the linear response to an electromagnetic field. The diamagnetic current is obtained by carrying out the expansion in \mathbf{A} to linear order in (20) and going over to momentum space. The result for the prefactor of $A_\nu(\mathbf{q})$ coming from the kinetic current in such an expansion is

$$\hat{T}_{\mu\nu}^K(\mathbf{q}) = -\frac{1}{N_c} \sum_{m,\ell,\sigma} \sum_{\mathbf{k}} (\beta_m^\ell)_\mu (\beta_m^\ell)_\nu \left[t_m^\ell e^{-i\mathbf{k}\cdot\beta_m^\ell} c_{m+\beta_m^\ell\sigma}^\dagger(\mathbf{k}) c_{m\sigma}(\mathbf{k}+\mathbf{q}) + t_m^{\ell*} e^{i(\mathbf{k}+\mathbf{q})\cdot\beta_m^\ell} c_{m\sigma}^\dagger(\mathbf{k}) c_{m+\beta_m^\ell\sigma}(\mathbf{k}+\mathbf{q}) \right] \quad (36)$$

There is also a pairing contribution $\hat{T}_{\mu\nu}^\Delta(\mathbf{q})$. However, since $\langle \hat{J}_\mu^\Delta(\mathbf{q}) \rangle \equiv 0$, this term does not contribute to the response of the current, and thus is irrelevant for our calculation of the superfluid weight.

Superfluid Weight

The superfluid weight may be computed by calculating the response of the current $\langle \hat{J}_\mu \rangle \equiv \langle \hat{J}_\mu^K \rangle$ to a static vector potential ($\omega = 0$) in the long wavelength limit ($\mathbf{q} \rightarrow 0$) [1, 2]

$$\delta \langle \hat{J}_\mu(\mathbf{q} \rightarrow 0, \omega = 0) \rangle \equiv \delta \langle \hat{J}_\mu^K(\mathbf{q} \rightarrow 0, \omega = 0) \rangle = D_{\mu\nu}^{(s)} A_\nu(\mathbf{q} = 0, \omega = 0) \quad (37)$$

where

$$D_{\mu\nu}^{(s)} = \left\langle \hat{T}_{\mu\nu}^K(\mathbf{q} = 0, \omega = 0) \right\rangle + \lim_{\mathbf{q} \rightarrow 0} \Pi_{\mu\nu}(\mathbf{q}, \omega = 0) \quad (38)$$

We will see that the pairing potential modifies the paramagnetic current-current correlation function $\Pi_{\mu\nu}(\mathbf{q}, \omega)$.

Paramagnetic Current-Current Correlation Function

We will compute the paramagnetic current-current correlation function while taking into account the dependence of the pairing potential on $A_\mu(\mathbf{q})$. We compute the following response function in imaginary time τ :

$$\Pi_{\mu\nu}(\mathbf{q}, \tau) = -\frac{1}{N_c} \left\langle \mathcal{T}_\tau \hat{J}_\mu^{K,p}(\mathbf{q}, \tau) \hat{J}_\nu^p(-\mathbf{q}, 0) \right\rangle \quad (39)$$

The time-ordering symbol in imaginary time is \mathcal{T}_τ . Note that the first factor in the expectation value above is the kinetic current operator $\hat{J}_\mu^{K,p}$, since we are computing the response of $\langle \hat{J}_\mu^K \rangle$, whereas the second factor is the full current $\hat{J}_\nu^p = \hat{J}_\nu^{K,p} + \hat{J}_\nu^\Delta$, since the vector potential couples to the full current.

The response function may be represented in the Matsubara frequency domain, using (32), as

$$\Pi_{\mu\nu}(\mathbf{q}, i\omega_n) = \frac{1}{\beta N_c} \sum_{mm'l'l'} \sum_{\mathbf{k}, ik_{n'}} \text{Tr} \left[\mathcal{G}_{m'l'}(\mathbf{k}, ik_{n'}) \cdot I_{l'l;\mu}^K(\mathbf{k}, \mathbf{q}) \cdot \mathcal{G}_{lm}(\mathbf{k} + \mathbf{q}, ik_{n'} + i\omega_n) \cdot I_{mm';\nu}(\mathbf{k} + \mathbf{q}, -\mathbf{q}) \right] \quad (40)$$

The centered dots indicate matrix multiplication in particle/hole space and \mathcal{G} can be expressed in the basis

$$\psi_m(\mathbf{k}) = \begin{pmatrix} c_{m\uparrow}(\mathbf{k}) \\ c_{m\downarrow}^\dagger(-\mathbf{k}) \end{pmatrix} \quad (41)$$

as

$$\mathcal{G}_{mm'}(\mathbf{k}, ik_{n'}) = - \int_0^\beta d\tau \left\langle \mathcal{T}_\tau \psi_m(\mathbf{k}, \tau) \psi_{m'}^\dagger(\mathbf{k}, 0) \right\rangle e^{ik_{n'}\tau} \quad (42)$$

which is a 2×2 matrix-valued Green's function; α and β label the orbital/site within the unit cell. $\omega_n = 2\pi n/\beta$ is a bosonic frequency and $k_{n'} = (2n' + 1)\pi/\beta$ is a fermionic frequency. It is convenient to express \mathcal{G} in terms of eigenstates $|\phi_a(\mathbf{k})\rangle$ with particle and hole components at site/orbital m

$$|\phi_a^m(\mathbf{k})\rangle = \begin{pmatrix} u_a^m(\mathbf{k}) \\ v_a^m(\mathbf{k}) \end{pmatrix} \quad (43)$$

and energies $E_a(\mathbf{k})$ of the BdG Hamiltonian as

$$\mathcal{G}_{mm'}(\mathbf{k}, ik_m) = \sum_a \frac{|\phi_a^m(\mathbf{k})\rangle\langle\phi_a^{m'}(\mathbf{k})|}{ik_{n'} - E_a(\mathbf{k})} \quad (44)$$

Inserting this into (40) and doing the sum over $k_{n'}$, we obtain, in the static limit $\omega_n = 0$,

$$\begin{aligned} \Pi_{\mu\nu}(\mathbf{q}, i\omega_n = 0) &= \frac{1}{N_c} \sum_{\mathbf{k}} \sum_{ab} \frac{n_F(E_a(\mathbf{k})) - n_F(E_b(\mathbf{k} + \mathbf{q}))}{E_a(\mathbf{k}) - E_b(\mathbf{k} + \mathbf{q})} \langle\phi_a(\mathbf{k})|I_{\mu}^K(\mathbf{k}, \mathbf{q})|\phi_b(\mathbf{k} + \mathbf{q})\rangle \\ &\quad \times \langle\phi_b(\mathbf{k} + \mathbf{q})|I_{\nu}(\mathbf{k} + \mathbf{q}, -\mathbf{q})|\phi_a(\mathbf{k})\rangle \end{aligned} \quad (45)$$

Where we have introduced the shorthand notation $\langle\phi_b(\mathbf{k})|M|\phi_a(\mathbf{k}')\rangle = \sum_{mm'} \langle\phi_b^m(\mathbf{k})|M_{mm'}|\phi_a^{m'}(\mathbf{k}')\rangle$. We then take the limit $\mathbf{q} \rightarrow 0$, where $I_{m\beta;\mu}(\mathbf{k}, \mathbf{q} \rightarrow 0)$ may be expressed as

$$I_{mm';\mu}(\mathbf{k}, 0) = \begin{pmatrix} \frac{\partial H_{mm'}}{\partial k_{\mu}}|_{\mathbf{k}} & \frac{\delta\Delta_m}{\delta Q_{\mu}}\delta_{mm'} \\ \frac{\delta\Delta_m^*}{\delta Q_{\mu}}\delta_{mm'} & -\frac{\partial H_{mm'}}{\partial k_{\mu}}|_{-\mathbf{k}} \end{pmatrix} \quad (46)$$

where H is the normal state Hamiltonian. We have called $A_{\mu}(\mathbf{q} = 0) = Q_{\mu}$. Note that $\frac{\delta\Delta_m}{\delta Q_{\mu}} \equiv \frac{\delta\Delta_m}{\delta A_{\mu}}|_0$ from the main text. We have

$$\Pi_{\mu\nu}(\mathbf{q} \rightarrow 0, i\omega_n = 0) = \frac{1}{N_c} \sum_{\mathbf{k}} \sum_{ab} \frac{n_F(E_a(\mathbf{k})) - n_F(E_b(\mathbf{k}))}{E_a(\mathbf{k}) - E_b(\mathbf{k})} \langle\phi_a(\mathbf{k})|I_{\mu}^K(\mathbf{k}, 0)|\phi_b(\mathbf{k})\rangle \langle\phi_b(\mathbf{k})|I_{\nu}(\mathbf{k}, 0)|\phi_a(\mathbf{k})\rangle \quad (47)$$

Note that the limit $\mathbf{q} \rightarrow 0$ implies that $\frac{n_F(E_a(\mathbf{k})) - n_F(E_b(\mathbf{k}))}{E_a(\mathbf{k}) - E_b(\mathbf{k})}$ should be understood as $\frac{\partial n_F}{\partial E}$ whenever $E_b(\mathbf{k}) = E_a(\mathbf{k})$.

Calculating the Response of Δ

In order to complete the calculation, we need to compute $\frac{\delta\Delta_m}{\delta Q_{\mu}}$. This can be done in a number of ways including finite difference as mentioned in the main text (also see below), differentiating the gap equations directly, solving the Bethe-Salpeter equation for the vertex correction, or using linear response. Here, we use linear response. The operator $\hat{\Delta}_m$ can be written in Nambu form by writing

$$\hat{\Delta}_m(\mathbf{q}) = U \sum_{\mathbf{k}} c_{m,\downarrow}(-\mathbf{k}) c_{m,\uparrow}(\mathbf{k} + \mathbf{q}) = U \sum_{\mathbf{k}} \sum_{ll'} \psi_l^{\dagger}(\mathbf{k}) \cdot \mathcal{M}_{ll'}^m \cdot \psi_{l'}(\mathbf{k} + \mathbf{q}) \quad (48)$$

where $\mathcal{M}_{ll'}^m = \delta_{ll'} \delta_{l,m} \tau_-$ and $\tau_- = \frac{1}{2}(\tau_x - i\tau_y)$ where τ_x and τ_y are the Pauli x and y matrices in particle/hole space. The centered dots indicate matrix multiplication in particle/hole space. We compute the response function

$$\begin{aligned} \frac{\delta\Delta_m}{\delta A_{\mu}(\mathbf{q}, \tau)} &= \frac{1}{N_c} \left\langle \mathcal{T}_{\tau} \hat{\Delta}_m(\mathbf{q}, \tau) J_{\mu}^p(-\mathbf{q}, 0) \right\rangle \\ &= \frac{U}{N_c} \sum_{\mathbf{k}\mathbf{k}'} \sum_{pl'l'p'} \left\langle \mathcal{T}_{\tau} \psi_p^{\dagger}(\mathbf{k}, \tau) \cdot \mathcal{M}_{pl}^m \cdot \psi_l(\mathbf{k} + \mathbf{q}, \tau) \psi_{l'}^{\dagger}(\mathbf{k}', 0) \cdot I_{l'p';\mu}(\mathbf{k}', -\mathbf{q}) \cdot \psi_{p'}(\mathbf{k}' - \mathbf{q}, 0) \right\rangle \end{aligned} \quad (49)$$

We have assumed that $\langle\Delta_m(\mathbf{q})\rangle = 0$ for $\mathbf{q} \neq 0$ and $\langle J_{\mu}^p(\mathbf{q} = 0)\rangle = 0$ (i.e. the total current vanishes in the groundstate). The above may be expressed in Matsubara frequency space as

$$\begin{aligned} \frac{\delta\Delta_m}{\delta A_{\mu}(\mathbf{q}, i\omega_n)} &= -\frac{U}{\beta N_c} \sum_{pp'pl'l'} \sum_{\mathbf{k}, ik_{n'}} \text{Tr} \left[\mathcal{G}_{p'l'}(\mathbf{k}, ik_{n'}) \cdot \mathcal{M}_{l'l}^m \cdot \mathcal{G}_{lp}(\mathbf{k} + \mathbf{q}, ik_{n'} + i\omega_n) \cdot I_{pp';\mu}(\mathbf{k} + \mathbf{q}, -\mathbf{q}) \right] \\ &= -\frac{U}{\beta N_c} \sum_{pp'} \sum_{\mathbf{k}, ik_{n'}} \text{Tr} \left[\mathcal{G}_{p'm}(\mathbf{k}, ik_{n'}) \cdot \tau_- \cdot \mathcal{G}_{mp}(\mathbf{k} + \mathbf{q}, ik_{n'} + i\omega_n) \cdot I_{pp';\mu}(\mathbf{k} + \mathbf{q}, -\mathbf{q}) \right] \end{aligned} \quad (50)$$

We follow the steps leading to (47), and we find

$$\frac{\delta\Delta_m}{\delta Q_\mu} = -\frac{U}{N_c} \sum_{\mathbf{k}} \sum_{ab} \frac{n_F(E_a(\mathbf{k})) - n_F(E_b(\mathbf{k}))}{E_a(\mathbf{k}) - E_b(\mathbf{k})} \langle \phi_a(\mathbf{k}) | \mathcal{M}^m | \phi_b(\mathbf{k}) \rangle \langle \phi_b(\mathbf{k}) | I_\mu(\mathbf{k}, 0) | \phi_a(\mathbf{k}) \rangle \quad (51)$$

$$= -\frac{U}{N_c} \sum_{\mathbf{k}} \sum_{ab} \frac{n_F(E_a(\mathbf{k})) - n_F(E_b(\mathbf{k}))}{E_a(\mathbf{k}) - E_b(\mathbf{k})} \langle \phi_a^m(\mathbf{k}) | \tau_- | \phi_b^m(\mathbf{k}) \rangle \langle \phi_b(\mathbf{k}) | I_\mu(\mathbf{k}, 0) | \phi_a(\mathbf{k}) \rangle \quad (52)$$

This is an equation in $\frac{\delta\Delta_m}{\delta Q_\mu}$ since this quantity also appears in the right hand side as

$$I_\mu(\mathbf{k}, 0) \equiv I_\mu^K(\mathbf{k}, 0) + \sum_m \left(\frac{\delta\Delta_m}{\delta Q_\mu} \mathcal{M}^{mT} + \frac{\delta\Delta_m^*}{\delta Q_\mu} \mathcal{M}^m \right) \quad (53)$$

where

$$I_\mu^K(\mathbf{k}, 0) \equiv I_\mu^K(\mathbf{k}) = \begin{pmatrix} \frac{\partial H}{\partial k_\mu} |_{\mathbf{k}} & 0 \\ 0 & -\frac{\partial H^*}{\partial k_\mu} |_{-\mathbf{k}} \end{pmatrix} \quad (54)$$

Plugging this in to the right hand side gives

$$\begin{aligned} \frac{\delta\Delta_m}{\delta Q_\mu} = & -\frac{U}{N_c} \sum_{\mathbf{k}} \sum_{ab} \frac{n_F(E_a(\mathbf{k})) - n_F(E_b(\mathbf{k}))}{E_a(\mathbf{k}) - E_b(\mathbf{k})} \langle \phi_a^m(\mathbf{k}) | \tau_- | \phi_b^m(\mathbf{k}) \rangle \langle \phi_b(\mathbf{k}) | I_\mu^K(\mathbf{k}) | \phi_a(\mathbf{k}) \rangle \\ & - \frac{U}{N_c} \sum_{m'} \frac{\delta\Delta_{m'}}{\delta Q_\mu} \sum_{\mathbf{k}} \sum_{ab} \frac{n_F(E_a(\mathbf{k})) - n_F(E_b(\mathbf{k}))}{E_a(\mathbf{k}) - E_b(\mathbf{k})} \langle \phi_a^m(\mathbf{k}) | \tau_- | \phi_b^m(\mathbf{k}) \rangle \langle \phi_b^{m'}(\mathbf{k}) | \tau_+ | \phi_a^{m'}(\mathbf{k}) \rangle \\ & - \frac{U}{N_c} \sum_{m'} \frac{\delta\Delta_{m'}^*}{\delta Q_\mu} \sum_{\mathbf{k}} \sum_{ab} \frac{n_F(E_a(\mathbf{k})) - n_F(E_b(\mathbf{k}))}{E_a(\mathbf{k}) - E_b(\mathbf{k})} \langle \phi_a^m(\mathbf{k}) | \tau_- | \phi_b^m(\mathbf{k}) \rangle \langle \phi_b^{m'}(\mathbf{k}) | \tau_- | \phi_a^{m'}(\mathbf{k}) \rangle \end{aligned} \quad (55)$$

where $\tau_+ = \frac{1}{2}(\tau_x + i\tau_y)$. This may be written in the following form

$$(C_\mu)_m = \sum_{m'} \left(\mathcal{A}_{mm'} \frac{\delta\Delta_{m'}}{\delta Q_\mu} + \mathcal{B}_{mm'} \frac{\delta\Delta_{m'}^*}{\delta Q_\mu} \right) \quad (56)$$

where

$$\begin{aligned} \mathcal{A}_{mm'} = & -\frac{1}{N_c} \sum_{\mathbf{k}} \sum_{ab} \frac{n_F(E_a(\mathbf{k})) - n_F(E_b(\mathbf{k}))}{E_a(\mathbf{k}) - E_b(\mathbf{k})} \langle \phi_a^m(\mathbf{k}) | \tau_- | \phi_b^m(\mathbf{k}) \rangle \langle \phi_b^{m'}(\mathbf{k}) | \tau_+ | \phi_a^{m'}(\mathbf{k}) \rangle - \frac{1}{U} \delta_{mm'} \\ \mathcal{B}_{mm'} = & -\frac{1}{N_c} \sum_{\mathbf{k}} \sum_{ab} \frac{n_F(E_a(\mathbf{k})) - n_F(E_b(\mathbf{k}))}{E_a(\mathbf{k}) - E_b(\mathbf{k})} \langle \phi_a^m(\mathbf{k}) | \tau_- | \phi_b^m(\mathbf{k}) \rangle \langle \phi_b^{m'}(\mathbf{k}) | \tau_- | \phi_a^{m'}(\mathbf{k}) \rangle \\ (C_\mu)_m = & \frac{1}{N_c} \sum_{\mathbf{k}} \sum_{ab} \frac{n_F(E_a(\mathbf{k})) - n_F(E_b(\mathbf{k}))}{E_a(\mathbf{k}) - E_b(\mathbf{k})} \langle \phi_a^m(\mathbf{k}) | \tau_- | \phi_b^m(\mathbf{k}) \rangle \langle \phi_b(\mathbf{k}) | I_\mu^K(\mathbf{k}) | \phi_a(\mathbf{k}) \rangle \end{aligned} \quad (57)$$

The vector C_μ corresponds to the first term on the right hand side of (55).

The equation (56) is singular. This follows from gauge invariance. Consider a small rotation of the phase of Δ_j

$$\Delta_j \rightarrow e^{i\alpha} \Delta_j \approx (1 + i\alpha) \Delta_j \quad (58)$$

where $\alpha \ll 1$. We may think of this as perturbing the Hamiltonian (1) with

$$\hat{\mathcal{H}}' = -i\alpha \sum_j \left(\Delta_j c_{j,\uparrow}^\dagger c_{j,\downarrow}^\dagger - \Delta_j^* c_{j,\downarrow} c_{j,\uparrow} \right) \quad (59)$$

We then compute the response of the pairing potential Δ_i to this static perturbation. On the one hand, the answer is clear, it is

$$\delta\Delta_m = i\alpha \Delta_m \quad (60)$$

On the other hand, the response $\delta\Delta_m$ follows from the static linear response formula, which may be written as

$$\begin{aligned}\delta\Delta_m &= \frac{U}{N_c} \sum_{\mathbf{k}} \sum_{ab} \frac{n_F(E_a(\mathbf{k})) - n_F(E_b(\mathbf{k}))}{E_a(\mathbf{k}) - E_b(\mathbf{k})} \langle \phi_a(\mathbf{k}) | \mathcal{M}^m | \phi_b(\mathbf{k}) \rangle \langle \phi_b(\mathbf{k}) | (-i\alpha\mathcal{M}^{mT}\Delta_m + i\alpha\mathcal{M}^m\Delta_m^*) | \phi_a(\mathbf{k}) \rangle \\ &= U \sum_{m'} \left(\mathcal{A}_{mm'} + \frac{1}{U} \delta_{mm'} \right) (i\alpha\Delta_{m'}) - U \sum_{mm'} \mathcal{B}_{mm'} (i\alpha\Delta_{m'}^*)\end{aligned}\quad (61)$$

Combining (60) and (61), we have

$$\sum_{m'} (\mathcal{A}_{mm'}\Delta_{m'} - \mathcal{B}_{mm'}\Delta_{m'}^*) = 0 \quad (62)$$

(This may be viewed as a Ward identity obeyed by the pairing susceptibility.) Thus, for any solution $\frac{\delta\Delta_{\tilde{i}}}{\delta Q_{\mu}}$ of (56), we may construct another solution

$$\frac{\delta\Delta_{\tilde{i}}}{\delta Q_{\mu}} \rightarrow \frac{\delta\Delta_{\tilde{i}}'}{\delta Q_{\mu}} = \frac{\delta\Delta_{\tilde{i}}}{\delta Q_{\mu}} + i\alpha\Delta_{\tilde{i}} \quad (63)$$

since according to (62), the additional term is “projected out.” The response (60) corresponds to the Goldstone mode, as is clear from (58). The matrix pseudoinverse is convenient for finding a representative solution of a singular equation such as (56).

Correction to the Superfluid Weight

Once $\frac{\delta\Delta_m}{\delta Q_{\mu}}$ is determined, we may compute the correction to the superfluid weight. It is expedient to write

$$\begin{aligned}(D_s)_{\mu\nu} &= \left\langle \hat{T}_{\mu\nu}^K(\mathbf{q} = 0, \omega = 0) \right\rangle + \frac{1}{N_c} \sum_{\mathbf{k}} \sum_{ab} \frac{n_F(E_a(\mathbf{k})) - n_F(E_b(\mathbf{k}))}{E_a(\mathbf{k}) - E_b(\mathbf{k})} \langle \phi_a(\mathbf{k}) | I_{\mu}^K(\mathbf{k}, 0) | \phi_b(\mathbf{k}) \rangle \langle \phi_b(\mathbf{k}) | I_{\nu}^K(\mathbf{k}, 0) | \phi_a(\mathbf{k}) \rangle \\ &= \left(D_s^{(0)} \right)_{\mu\nu} + \frac{1}{N_c} \sum_{\mathbf{k}} \sum_{ab} \sum_m \frac{n_F(E_a(\mathbf{k})) - n_F(E_b(\mathbf{k}))}{E_a(\mathbf{k}) - E_b(\mathbf{k})} \langle \phi_a(\mathbf{k}) | I_{\mu}^K(\mathbf{k}, 0) | \phi_b(\mathbf{k}) \rangle \langle \phi_b(\mathbf{k}) | \left(\frac{\delta\Delta_m}{\delta Q_{\nu}} \mathcal{M}^{mT} + \frac{\delta\Delta_m^*}{\delta Q_{\nu}} \mathcal{M}^m \right) | \phi_a(\mathbf{k}) \rangle \\ &= \left(D_s^{(0)} \right)_{\mu\nu} + 2 \operatorname{Re} \left[\sum_m (C_{\mu})_m \frac{\delta\Delta_m^*}{\delta Q_{\nu}} \right]\end{aligned}\quad (64)$$

where

$$\left(D_s^{(0)} \right)_{\mu\nu} = \left\langle \hat{T}_{\mu\nu}^K(\mathbf{q} = 0, \omega = 0) \right\rangle + \Pi_{\mu\nu}^{(0)}(\mathbf{q} \rightarrow 0, i\omega_n = 0) \quad (65)$$

is the usual formula for the superfluid weight and

$$\Pi_{\mu\nu}^{(0)}(\mathbf{q} \rightarrow 0, i\omega_n = 0) = \frac{1}{N_c} \sum_{\mathbf{k}} \sum_{ab} \frac{n_F(E_a(\mathbf{k})) - n_F(E_b(\mathbf{k}))}{E_a(\mathbf{k}) - E_b(\mathbf{k})} \langle \phi_a(\mathbf{k}) | I_{\mu}^K(\mathbf{k}, 0) | \phi_b(\mathbf{k}) \rangle \langle \phi_b(\mathbf{k}) | I_{\nu}^K(\mathbf{k}, 0) | \phi_a(\mathbf{k}) \rangle \quad (66)$$

Therefore the correction to the superfluid weight due to the response of the pairing potential is

$$(\delta D_s)_{\mu\nu} = 2 \operatorname{Re} \left[\sum_m (C_{\mu})_m \frac{\delta\Delta_m^*}{\delta Q_{\nu}} \right] \quad (67)$$

$$= \frac{1}{N_c} \sum_{\mathbf{k}} \sum_{ab} \sum_m \frac{n_F(E_a(\mathbf{k})) - n_F(E_b(\mathbf{k}))}{E_a(\mathbf{k}) - E_b(\mathbf{k})} \langle \phi_a(\mathbf{k}) | I_{\mu}^K(\mathbf{k}, 0) | \phi_b(\mathbf{k}) \rangle \quad (68)$$

$$\times \left(\frac{\delta\Delta_m}{\delta Q_{\nu}} \langle \phi_b^m(\mathbf{k}) | \tau_+ | \phi_a^m(\mathbf{k}) \rangle + \frac{\delta\Delta_m^*}{\delta Q_{\nu}} \langle \phi_b^m(\mathbf{k}) | \tau_- | \phi_a^m(\mathbf{k}) \rangle \right) \quad (69)$$

where we have used the expression for C_{μ} is given in (57). Eq. (68) is the response of the current due to the change in the pairing potential induced by a “twist” \mathbf{Q} .

Example: Uniform Superconductor

We show that $(\delta D_s)_{\mu\nu}$ vanishes for a uniform s -wave system. It is sufficient to show that C_μ vanishes. The Hamiltonian is

$$\mathcal{H} = \sum_{\mathbf{k}\sigma} \xi_{\mathbf{k}} c_{\mathbf{k}\sigma}^\dagger c_{\mathbf{k}\sigma} - \Delta \sum_{\mathbf{k}} c_{\mathbf{k}\uparrow}^\dagger c_{-\mathbf{k}\downarrow}^\dagger - \Delta^* \sum_{\mathbf{k}} c_{-\mathbf{k}\downarrow} c_{\mathbf{k}\uparrow} \quad (70)$$

where V is the volume of the system. Let us take Δ to be real. The Green's function is then

$$\mathcal{G}(\mathbf{k}, ik_n) = \frac{ik_n + \xi_{\mathbf{k}} \tau_3 + \Delta \tau_1}{(ik_n)^2 - E_{\mathbf{k}}^2} \quad (71)$$

where $E_{\mathbf{k}}^2 = \xi_{\mathbf{k}}^2 + \Delta^2$. It is convenient to express C_μ as

$$\begin{aligned} C_\mu &= -\frac{1}{\beta V} \lim_{\mathbf{q} \rightarrow 0} \sum_{\mathbf{k}, ik_n} (\partial_\mu \xi_{\mathbf{k}}) \text{Tr} [\tau_- \cdot \mathcal{G}(\mathbf{k} + \mathbf{q}, ik_n) \cdot \mathcal{G}(\mathbf{k}, ik_n)] \\ &= -\frac{1}{V} \sum_{\mathbf{k}} (\partial_\mu \xi_{\mathbf{k}}) \frac{\Delta}{2E_{\mathbf{k}}} (n'_F(E_{\mathbf{k}}) - n'_F(-E_{\mathbf{k}})) \\ &= 0 \end{aligned} \quad (72)$$

where $\partial_\mu = \partial/\partial k_\mu$. The last equality follows from the fact that $n'_F(-E_{\mathbf{k}}) = n'_F(E_{\mathbf{k}})$. Thus the correction (68) vanishes, and a spatially non-uniform system is required for the correction to be non-zero.

Relation to Vertex Corrections

We briefly sketch how our result may be obtained using current vertex corrections in the Nambu basis. In a superconductor, the photon vertex function Γ^μ describes the coupling of the system to the electromagnetic vector potential A_μ . This can be related to the bare vertex γ^μ (e.g., determined through minimal or Peierls substitution), and the correction arising from interactions encoded in the self-energy Σ :

$$\Gamma^\mu - \gamma^\mu = \frac{\delta \Sigma}{\delta A_\mu}. \quad (73)$$

In terms of Green's functions, the electromagnetic kernel is expressed as:

$$\Pi^{\mu\nu}(q) = -i \text{Tr} \left[\int d^4 k \gamma^\mu(k + q, k) \mathcal{G}(k) \Gamma^\nu(k, k + q) \mathcal{G}(k + q) \right], \quad (74)$$

where $\mathcal{G}(k)$ is the full Green's function in the Nambu basis. The self-energy Σ may depend on A_μ , either directly, or indirectly through the order parameter. Indeed, in BCS/BdG theory, the self-energy in the Nambu basis is given by

$$\Sigma(k) = \begin{pmatrix} 0 & \Delta(k) \\ \Delta^\dagger(k) & 0 \end{pmatrix} \quad (75)$$

Thus the correction to the electromagnetic kernel is patently given by a term proportional to $\delta \Delta / \delta A_\mu$. One may solve for this correction using the Bethe-Salpeter equation, and it can be shown that this formulation respects gauge invariance via the generalized Ward identity [3].

Gauge Invariance

Physical observables, in particular the correction to the superfluid weight arising from the fluctuations in Δ , must be invariant under global $U(1)$ gauge transformations. This implies that the overall phase of the $\{\Delta_m(\mathbf{Q})\}$ can vary in an arbitrary way as a function of the probe field \mathbf{Q} . To clarify the point at issue, let us suppose that there

exists a choice of the overall phase such that $\{\Delta_m(\mathbf{Q})\}$ are smooth functions of \mathbf{Q} in the neighborhood of $\mathbf{Q} = 0$. We may thus approximate

$$\frac{\delta\Delta_m}{\delta Q_i} \approx \frac{\Delta_m(\delta Q \hat{\mathbf{e}}_i) - \Delta_m(0)}{\delta Q} \quad (76)$$

for δQ sufficiently small. This approximation for determining $\frac{\delta\Delta_m}{\delta Q_i}$ may be most convenient when one has numerical solutions of $\{\Delta_m(\mathbf{Q})\}$ for various \mathbf{Q} . However, numerical solutions of $\{\Delta_m(\mathbf{Q})\}$ are not guaranteed to possess a smoothly varying phase as a function of \mathbf{Q} . This is especially salient in systems with vortices, where the singular nature of the phase around vortex cores means that, in general, the phase does not vary smoothly. Let us suppose that the numerical solution $\{\Delta'_m(\mathbf{Q})\}$ differs from the smooth solution $\{\Delta_m(\mathbf{Q})\}$ by a phase: $\Delta'_m(\delta Q \hat{\mathbf{e}}_i) = \Delta_m(\delta Q \hat{\mathbf{e}}_i) e^{i\theta(\delta Q \hat{\mathbf{e}}_i)}$ and $\Delta'_m(0) = \Delta_m(0)$. Then, using the approximation Eq. (76), we would find

$$\frac{\delta\Delta'_m}{\delta Q_i} \approx \frac{\Delta'_m(\delta Q \hat{\mathbf{e}}_i) - \Delta'_m(0)}{\delta Q} = \frac{\Delta_m(\delta Q \hat{\mathbf{e}}_i) e^{i\theta(\delta Q \hat{\mathbf{e}}_i)} - \Delta_m(0)}{\delta Q} \quad (77)$$

$$\approx \left(\frac{e^{i\theta(\delta Q \hat{\mathbf{e}}_i)} - 1}{\delta Q} \right) \Delta_m(0) + \frac{\delta\Delta_m}{\delta Q_i} \quad (78)$$

Again, since smoothness is not guaranteed, $e^{i\theta(\delta Q \hat{\mathbf{e}}_i)} - 1$ need not be small. Therefore, in order that the result for δD_s be gauge invariant, it should return the same result whether $\frac{\delta\Delta'_m}{\delta Q_i}$ or $\frac{\delta\Delta_m}{\delta Q_i}$ is substituted into the formula. Equivalently, it should “project out” terms of the form $z_i \Delta_m(0)$ where $z_i = \frac{e^{i\theta(\delta Q \hat{\mathbf{e}}_i)} - 1}{\delta Q}$ is a (large) complex number.

We note that this is more restrictive than standard discussions of gauge invariance, since we allow arbitrarily rapid phase variations in the order parameter. This is essential for computing $\delta\Delta_m/\delta Q_i$ via finite difference approximation. In contrast, solutions to Eq. (56) are defined modulo a constant corresponding to an imaginary z_i (see Eq. (63)). This corresponds to the collective mode which is projected out, according to the generalized Ward identity (see previous section), thus ensuring gauge invariance. However, when using the finite difference approximation, both real and imaginary components of z_i must be projected out, as we have argued in the previous paragraph. We will argue that Eq. (67) is gauge-invariant in this latter sense. As we have mentioned below Eq. (67), δD_s is determined by the response of the current due to the change in the pairing potential. In other words, it is determined by the crossed susceptibility $\chi_{J,\Delta}$. Using this identification of the correction to the superfluid stiffness with the current-pairing susceptibility, we may see why it is gauge invariant according to the discussion above, provided scaling the pairing potential by a complex number produces no total current response in equilibrium. Consider an inhomogeneous superconductor described by a position-dependent pairing potential $\Delta(\mathbf{r})$. The current density $\mathbf{J}(\mathbf{r})$ in such a system is given by

$$\mathbf{J}(\mathbf{r}) \propto \text{Im}(\Delta^*(\mathbf{r})(\nabla + 2i\mathbf{A})\Delta(\mathbf{r})), \quad (79)$$

where $\Delta(\mathbf{r}) = |\Delta(\mathbf{r})|e^{i\theta(\mathbf{r})}$ is the complex pairing potential. In equilibrium, the total current is zero:

$$\mathbf{J}_{\text{tot}} = \int \mathbf{J}(\mathbf{r}) d\mathbf{r} = 0, \quad (80)$$

We now scale the pairing potential by a complex number $z = |z|e^{i\phi}$. The scaled pairing potential is

$$\Delta'(\mathbf{r}) = z\Delta(\mathbf{r}) = |z|e^{i\phi}\Delta(\mathbf{r}) = |z||\Delta(\mathbf{r})|e^{i(\theta(\mathbf{r})+\phi)}. \quad (81)$$

To determine the effect of this scaling on the current density, we compute the new current density $\mathbf{J}'(\mathbf{r})$ for the scaled pairing potential:

$$\mathbf{J}'(\mathbf{r}) \propto \text{Im}((\Delta'(\mathbf{r}))^*(\nabla + 2i\mathbf{A})\Delta'(\mathbf{r})). \quad (82)$$

Therefore, the new current density is

$$\mathbf{J}'(\mathbf{r}) \propto \text{Im}(|z|^2 \Delta^*(\mathbf{r})(\nabla + 2i\mathbf{A})\Delta(\mathbf{r})) = |z|^2 \text{Im}(\Delta^*(\mathbf{r})(\nabla + 2i\mathbf{A})\Delta(\mathbf{r})) = |z|^2 \mathbf{J}(\mathbf{r}). \quad (83)$$

Since $\mathbf{J}_{\text{tot}} = 0$, it follows that

$$\mathbf{J}'_{\text{tot}} = |z|^2 \mathbf{J}_{\text{tot}} = 0. \quad (84)$$

Thus, the change in the total current (the induced current response) due to scaling the pairing potential is

$$\delta\mathbf{J}_{\text{tot}} = 0. \quad (85)$$

We have verified numerically that Eq. (67) projects out $\frac{\delta\Delta_m}{\delta Q_i} = z_i \Delta_m$, and that it gives the same result under arbitrary variations in the phase $\theta(\mathbf{q})$, in the ground state for all cases studied in this work, thus achieving gauge invariance.

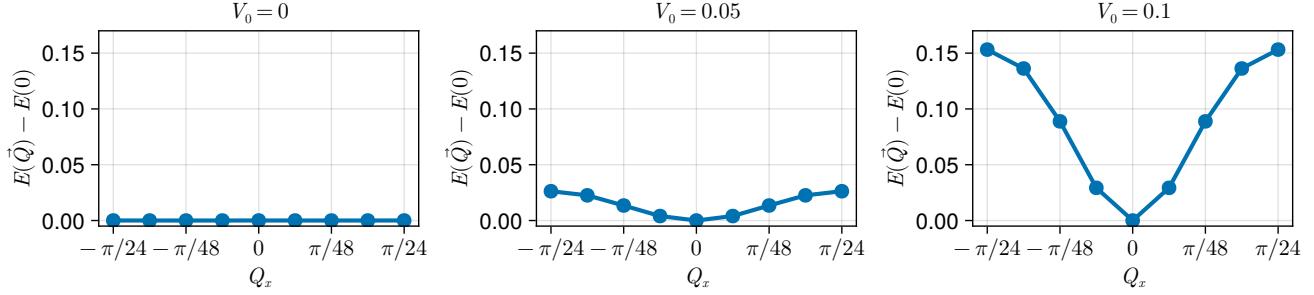


FIG. 1. The energy as a function of Q_x for the system corresponding to Fig. 2 of the main text. The cyan points in that figure are computed by taking a numerical second derivative at the minimum of the energy using Q points very close to that value (not shown here). Without a periodic potential ($V_0 = 0$), the system forms a vortex lattice that freely moves as Q is varied. Thus, the energy does not depend on Q , as seen in the left panel, and the superfluid weight vanishes. When a periodic potential is applied, the vortices become somewhat obstructed (pinned), resulting in the reemergence of superfluid weight (center and right panels).

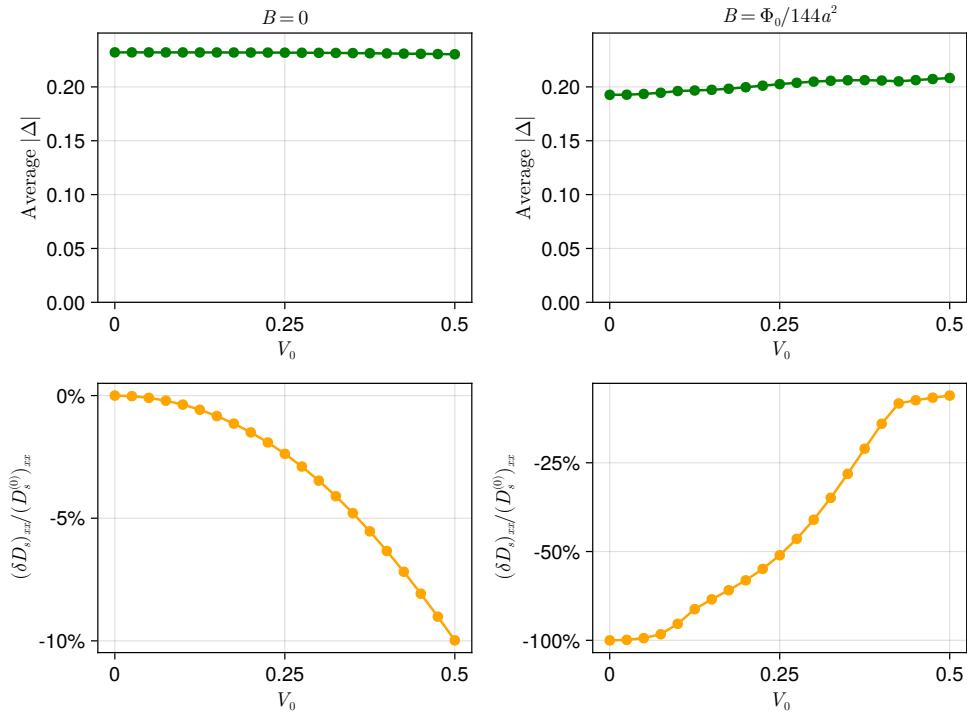


FIG. 2. Top row: the spatially averaged value of $|\Delta|$ as a function of the strength of the applied potential without (left) and with (right) an applied magnetic field. Areas with high potential $V(\mathbf{r})$ tend to reduce $|\Delta|$, while areas with low potential tend to enhance it, resulting in $|\Delta|$ roughly maintaining its average as V_0 increases. Bottom Row: The correction to the superfluid weight due to the response of Δ , expressed as a percentage of $D_s^{(0)}$, the uncorrected superfluid weight, without (left) and with (right) an applied magnetic field. Under an applied magnetic field, a vortex lattice forms, and if the vortices are unpinned ($V_0 = 0$), the correction completely eliminates the superfluid weight, which is incorrectly given as non-zero according to $D_s^{(0)}$. This is seen from the -100% correction shown in the bottom right panel at $V_0 = 0$.

Inversion of Equation (12)

As stated in the main text the square matrix K that appears in Eq. (12) in the main text is singular, it has rank one less than its dimension, n , reflecting the fact that the superconducting order parameter is defined apart from an overall phase factor. To obtain $\delta\Delta_m/\delta A_\mu|_0$ we need to calculate the pseudoinverse, \tilde{K} , of K . To do this we first perform a single-value-decomposition (SVD) of K :

$$K = U\Lambda V^\dagger \quad (86)$$

where U and V are $n \times n$ unitary matrices and Λ is a $n \times n$ diagonal matrix of the form

$$\Lambda = \begin{pmatrix} \lambda_1 & 0 & \cdots & \cdots & 0 \\ 0 & \lambda_2 & 0 & \cdots & 0 \\ \vdots & 0 & \lambda_3 & 0 & 0 \\ \vdots & \vdots & \vdots & \ddots & \vdots \\ 0 & 0 & 0 & 0 & \lambda_n = 0 \end{pmatrix}. \quad (87)$$

Let

$$\tilde{\Lambda} = \begin{pmatrix} \lambda_1^{-1} & 0 & \cdots & \cdots & 0 \\ 0 & \lambda_2^{-1} & 0 & \cdots & 0 \\ \vdots & 0 & \lambda_3^{-1} & 0 & 0 \\ \vdots & \vdots & \vdots & \ddots & \vdots \\ 0 & 0 & 0 & 0 & \tilde{\lambda}_n = 0 \end{pmatrix}. \quad (88)$$

then, the pseudoinverse of K is given by

$$\tilde{K} = V\tilde{\Lambda}U^\dagger \quad (89)$$

and

$$\left. \frac{\delta\Delta_m}{\delta A_\mu} \right|_0 = \tilde{K}C_\mu + (1 - \tilde{K}K)W \quad (90)$$

where C_μ is the column vector with elements $\{(C_\mu)_m\}$, and W is the vector containing the free parameters. In our case, only the last element of the diagonal matrix $(1 - \tilde{K}K)$ is nonzero leaving just one free parameter, corresponding to the overall gauge phase factor.

Superconductor with vortex lattice

We consider a superconductor with a 2D vortex lattice in the (x, y) plane induced by a background perpendicular magnetic field B_z . The presence of this field is taken into account within the tight model Hamiltonian (1) via the introduction of a Peierls phase. This has the effect of altering the translation group of the underlying square lattice to that of the magnetic translation group [4]. A magnetic unit cell must be chosen such that an integer number of magnetic flux quanta $\Phi_0 = h/e$ due to B_z thread the 2D systems. We chose the magnetic unit cells to be $Ma \times Ma$ with one flux quantum threading it.

- [1] D. J. Scalapino, S. R. White, and S. Zhang, Superfluid density and the drude weight of the hubbard model, *Physical Review Letters* **68**, 2830 (1992).
- [2] D. J. Scalapino, S. R. White, and S. Zhang, enInsulator, metal, or superconductor: The criteria, *Physical Review B* **47**, 7995 (1993).
- [3] J. R. Schrieffer, [Theory of Superconductivity](#), revised printing ed., Advanced Book Classics (CRC Press, Boca Raton London New York, 1964).
- [4] D. R. Hofstadter, Energy levels and wave functions of Bloch electrons in rational and irrational magnetic fields, *Physical Review B* **14**, 2239 (1976), publisher: APS.